

Adsorption Thermodynamics, Kinetics and Mechanism for the Adsorption of Erythromycin Onto Multi-Walled Carbon Nanotubes

Mahadethe Dashtizade¹, Davoud Balarak²

- 1- Department of Environmental Health, Student Research Committee, Zahedan University of Medical Sciences, Zahedan, Iran
 - 2- Department of Environmental Health, Health Promotion Research Center, School of Public Health, Zahedan University of Medical Sciences, Zahedan, Iran
- Corresponding author: E-mail: dbalarak2@gmail.com

Original Research Article

ABSTRACT

The ability of multi-walled carbon nanotubes (MWCNT) to adsorb the Erythromycin antibiotic from aqueous solution was studied through the batch experiments. The adsorption of Erythromycin onto MWCNT was found to be dependent on adsorbent dose, initial concentration and contact time. The experiments were carried out at natural solution pH. Based on the observed results, the highest removal efficiency was achieved to be 99.4% under optimum conditions. The adsorption kinetic results showed that the pseudo-second order model was more suitable to explain the adsorption of Erythromycin onto MWCNT. The adsorption mechanism results showed that the adsorption process was controlled by both the internal and external diffusion of Erythromycin molecules. The values of free energy change (ΔG^0) and enthalpy change (ΔH^0) revealed that the adsorption process has the spontaneous, feasible, and endothermic nature.

Keywords: Batch adsorption; MWCNT; Erythromycin; Kinetic; Thermodynamics.

1. INTRODUCTION

In recent years, antibiotics have been recognized as one of the most important water contaminants [1, 2]. Antibiotics are designed specifically as a drug to treat or to prevent the infectious diseases in human or animal body [3, 4]. The use of antibiotics has become an indispensable in human life and the global market consumption of these drugs increase steadily every year [5, 6]. For preventing or treating infections in humans or animals, only some parts of the antibiotics given dose are metabolized and the rest is excreted as the active compound [7, 8]. The emergence of resistant bacterial strains is considered as an issue associated with the abuse of antibiotics, which it can lead to serious public health crisis in the future [9, 10]. Antibiotics have been found in the water environment, including in wastewater, seawater treatment plants, surface water, groundwater, and even in drinking water [11].

Erythromycin, a 14-carbon macrolide, is generated by fermentation of *Streptomyces erythreus* and is used for treatment of various infections, especially the respiratory and skin diseases [12]. The similarity in its activity to penicillin is led to be considered as a substitute for penicillin against the Gram-positive bacteria in the people who are sensitive to penicillin. Furthermore, it is also consumes against *Mycoplasma*, *Campylobacter* and *Legionella* [13].

Although the elimination of the antibiotics from the wastewaters has been reported to be expensive; however this wastewater must be satisfactorily treated prior to the release into the environment [14]. The adsorption process, among the various process applied for treatment of wastewater containing antibiotics, is found as the most effective and efficient method [15, 16].

Compared to other process, e.g., the distillation or solvent extraction from diluted aqueous solutions, this process has achieved a great endorsement for large-scale separation from

liquid, since it is a process that need to low energy for adsorptive separation [17, 18]. Adsorption is a physical–chemical process that involves the mass transfer of a solute (adsorbate) from the fluid phase to the sorbent surface till the thermodynamic equilibrium of the adsorbate concentration is attained, with no further net adsorption [19].

Carbon Nanotubes (CNTs) have been studied extensively in last decade for different applications including water purification due to their extraordinary physiochemical properties associated with their small size, tubular morphology and ease of functionalization [20]. CNTs have been used for removal of antibiotics, dyes and heavy metals from its aqueous solution [21-23].

The major goal of this study is the evaluation of the MWCNTs ability for removal of Erythromycin from aqueous solution. The effects of several operating parameters such as adsorbent dose, initial Erythromycin concentration, mixing rate, contact time, and temperature on the Erythromycin adsorption at fixed pH=7 were investigated. The adsorption behavior of MWCNT towards Erythromycin removal was studied using kinetics and thermodynamic viewpoints.

2. MATERIALS AND METHODS

The multi-wall carbon nanotubes (MWCNT) used in this study had the purity more than 98% and provided from Research Institute of Petroleum Industry (RIPI), Tehran, Iran). The size and morphology of MWCNT were examined by scanning electron microscope (JEOL JSM 6500F) and transmission electron microscopy (TEM) (using a Philips XL30). The specific surface area of the adsorbent was determined by the BET method using a Gemini 2357 surface area analyzer (Micromeritics Instrument Corporation, USA).

Erythromycin (Fig. 1), an antibiotic, with a molecular formula of $C_{37}H_{67}NO_{13}$, molecular weight 733.93, $\lambda_{\max}$ of 280 nm, and C.I. number of 114-07-8, was chosen as a model antibiotic for the present experimental studies. The stock solution of Erythromycin (500 mg/L) was prepared by dissolving 500 mg of Erythromycin powder in 1000 mL of distilled water. The stock solution was diluted with distilled water to obtain the solutions with desired concentrations (10–100 mg/L).

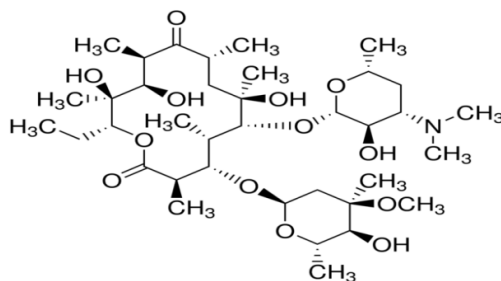


Fig 1. Chemical structure of Erythromycin

Batch Adsorption Test and Optimization of Conditions

The adsorption experiment was carried out in batch system inside 250 mL Erlenmeyer flasks containing 100 mL of synthetic Erythromycin solution. Initial pH of the samples was set by 0.1 molar NaOH and HCl. Afterwards, 0.4 g/L of adsorbent were added to the solutions with Erythromycin initial concentration of 25 ppm. The final solution was stirred at 30 °C and 120 rpm for 75 min. The solutes were filtered through the filter paper and 5 mL of the solution was analyzed to measure the adsorbed Erythromycin concentration. The optimization process

was also repeated for other parameters. These parameters were adsorbent dosage (0.1–1 g/L), mixing rate (0–200 rpm), and initial concentration of Erythromycin ion in the solution (10–100 ppm). To obtain the optimum condition, after adjusting the contact time to equilibrium condition, the desired parameter was varied at the determined range while other parameters were kept constant. The optimum condition of each parameter was selected and the investigation continued to define the optimum condition of other parameters. The Erythromycin concentration was identified by spectrophotometer at 280 nm (model DR-5000). In this research, all of the tests performed twice and the best results were reported. The amount of adsorbed ions by adsorbent for each gram of adsorbent is identified by following Eq [23, 24]:

$$q_e = \frac{(C_0 - C_e)}{W} \times V$$

Where q_e is the amount of adsorbed Erythromycin per gram of MWCNT (mg/g) in the equilibrium state, C_0 and C_e are initial and equilibrium concentrations of Erythromycin (mg/L), V is the solution volume and W is the weight of the MWCNT.

3. RESULTS AND DISCUSSION

Fig. 2 displays the surface morphology of MWCNTs. The SEM and TEM figures show that the MWCNTs were cylindrical and the range of main external and internal diameters was 2–3.5 and 1.2–1.7 nm, respectively. The specific surface area of the adsorbent used in this study was 782.8 m²/g.

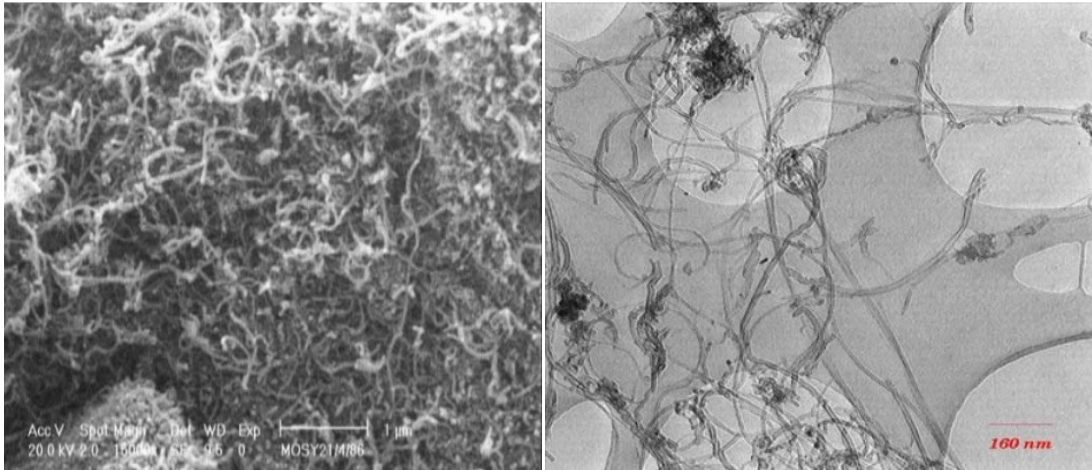


Fig. 2. Micrographs of MWCNTs (a) SEM and (b) TEM.

Effect of contact time and temperature: In order to establish the equilibrium time for Erythromycin adsorption onto MWCNT, the effect of contact time during the process was investigated until equilibrium reached. As shown in Fig. 3 the removal efficiency increases rapidly (in the first 75 min) due to the abundant availability of active binding site of the adsorbent and then remained almost constant with the occupancy of these sites [25-27]. Since the removal efficiency did not increase by increasing the time after 75 min, this time was applied as the equilibrium time for further experiments.

The effect of temperature on adsorption of Erythromycin onto MWCNT was conducted at 15, 25, 35 and 45 °C (288-318 K). Results presented in Fig. 3 and showed that the adsorption increases significantly with an increase in temperature from 288 K (adsorption capacity= 104.8 and removal efficiency= 83.71%) to 318 K (adsorption capacity= 124.6 and removal efficiency= 99.68%), which it illustrates that the adsorption process is endothermic. The increase in the adsorption capacity with temperature may be attributed to either change in pore size of the adsorbent improving intra-particle diffusion within the pores or enhancement in the chemical affinity of Erythromycin to the surface of the adsorbent [28]. This leads to increasing the disorder at the MWCNT surface and intensification of chemical interactions that take place during the adsorption process and as a result, increasing the adsorption capacity [29, 30].

Effect of Mixing Rate: The mixing rate and turbulence inside the aqueous solution is an important parameter in adsorption process because an increase in mixing rate increases the possibility of contact between the adsorbent and Erythromycin molecules which it results in higher efficiency. In order to examine the mixing rate on adsorption process, the parameters were determined in laboratory conditions as mixing rate of 0–200 rpm, initial Erythromycin concentration of 100 ppm, time of 75 min, temperature of 30 °C, adsorbent dosage of 0.8 g/L and pH = 7. The magnetic mixer was used for mixing process and the effect of this parameter is shown in Fig. 4. According to the Fig. 4, increasing the mixing rate in the range of 0–200 rpm increases the Erythromycin adsorption efficiency by the adsorbent. Higher mixing rate means the possibility of higher contact between the active sites and Erythromycin [30, 31]. The optimum removal was observed to be 98.9% at mixing rate of 200 rpm.

Effect of Adsorbent Dose: The adsorbent dosage is a considerable parameter in the adsorption process, as it determines the adsorption capacity in a certain concentration of adsorbed material. The experimental parameters for evaluation of the effect of MWCNT dosage (0.2–2 g/L) to remove the Erythromycin were the initial concentration of 100 ppm, temperature of 30 °C, contact time of 75 min, mixing rate of 200 rpm, pH of 7. Fig 5 shows the effect of MWCNT dose on adsorption of Erythromycin. The findings revealed that increasing the amount of used adsorbent leads to increase the Erythromycin adsorption, as the higher dosage increases the number of active sites for adsorption of Erythromycin ion [32, 33]. Increase in the amount of adsorbent up to 1 g/L results in the higher Erythromycin adsorption efficiency that is 92.7% . Higher dosages of adsorbent in aqueous solution, more than 1 g/L, show a negligible increase in adsorption because of saturation inactive sites [34]. Even, in some cases, the final adsorption is reduced because there was the higher possibility of contact between adsorbent particles and active sites and this factor makes flocculation on the sites and, ultimately, it decreases the number of active sites and adsorbent surfaces and, consequently, the final efficiency.

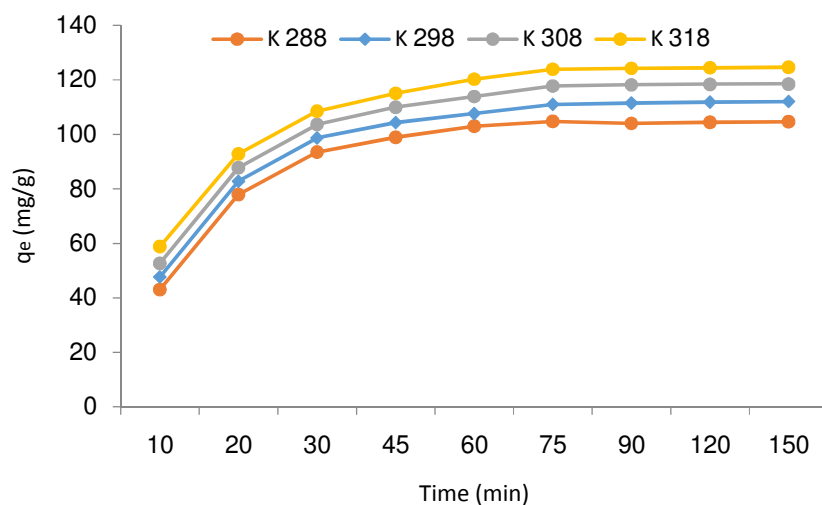


Fig 3. Effect of contact time and temperature on Erythromycin removal (pH =7, Adsorbent dosage 0.8 g/L, mixing rate 200 rpm, $C_0 = 100$ mg/L)

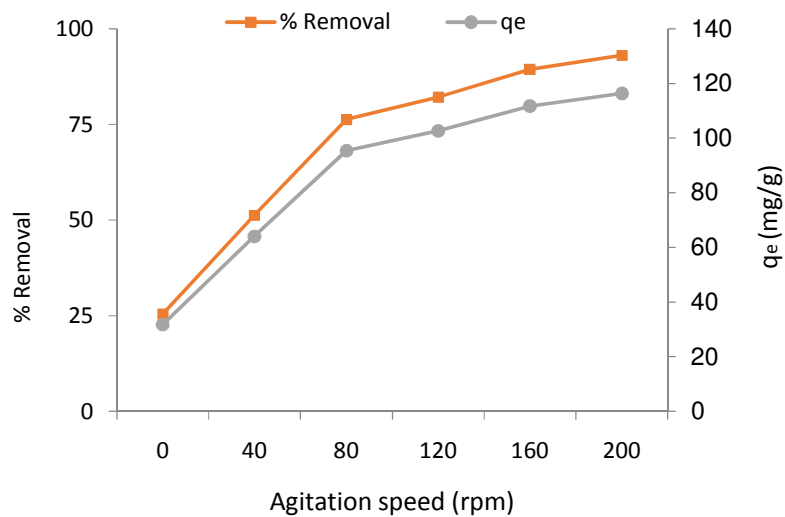


Fig. 4. Effect of mixing rate on Erythromycin adsorption ($C_0 = 100$ mg/L, temp= $25 \pm 2^\circ\text{C}$, time 75 min, adsorbent dosage 0.8 g/L, pH = 7)

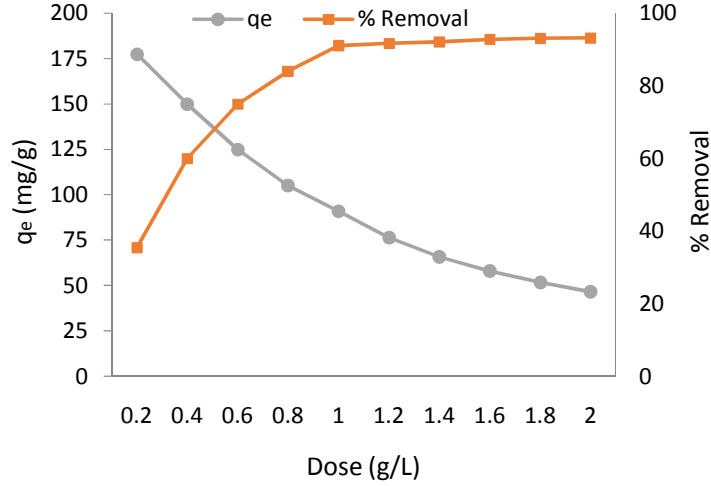


Fig 5: Effect of adsorbent dosage on Erythromycin adsorption ($C_0 = 100$ mg/L, time = 75 min, pH = 7, temp= $25 \pm 2^\circ\text{C}$ and mixing rate 200 rpm)

Adsorption thermodynamics

The thermodynamics for Erythromycin removal by MWCNTs was investigated in the temperature range of 288-318 K, and the influence of temperature on the adsorption capacity is shown in Fig. 3. It can be found that there is an increase in the adsorption capacity of MWCNTs with increasing the temperature. Thermodynamic parameters such as the change in Gibbs free energy (ΔG^0), enthalpy (ΔH^0) and entropy (ΔS^0) were determined using the following equation [34, 35]:

$$K = q_e / C_e$$

$$\Delta G = -RT \ln K$$

$$\ln K = \frac{\Delta S^0}{R} - \frac{\Delta H^0}{RT}$$

Table 1 summarizes the thermodynamic parameters associated with the adsorption process. Values of ΔG^0 were calculated from the values of adsorption equilibrium constant (K) using above equations. The negative values of ΔG^0 at the three temperatures show that the adsorption process is spontaneous and the degree of spontaneity increases with increasing the temperature [36, 37]. The values of ΔH^0 and ΔS^0 are calculated from the slope and the intercept of the linear plot of $\ln K$ vs. $1/T$. The overall adsorption process seems to be endothermic ($\Delta H^0 = 76.25$ KJ/mol). This result also supports the suggestion that the adsorption capacity of MWCNTs increases with increasing temperature. Table 1 also reveals that the ΔS^0 value is positive (entropy increases as a result of adsorption). A positive value of ΔS^0 reflects the affinity of the adsorbent to the Erythromycin, which is due to redistribution of energy between the adsorbate and adsorbent [38].

Table 1: Thermodynamic parameters of the Erythromycin adsorption onto MWCNT

T (K)	ΔG° (kJ mol ⁻¹)	ΔS° (J mol ⁻¹ K ⁻¹)	ΔH° (kJ mol ⁻¹)
288	-4.54	0.277	76.25
298	-5.71		
308	-8.24		
318	-13.11		

Adsorption kinetics

Fig . 3 demonstrate the effect of contact time on Erythromycin adsorption onto MWCNTs. It is found that the adsorption kinetics of Erythromycin onto MWCNT included two steps: a fast initial adsorption followed by a slow gradual adsorption. The initial rapid phase (first 30 min) accounted for a considerable portion of the adsorption. During this stage, about 80% of Erythromycin was adsorbed, which can be attributed to the rapid diffusion of Erythromycin molecules from the solution to the external surface of MWCNT. Adsorption in the subsequent time was slower and was probably due to the diffusion of Erythromycin molecules into the porous structures of the adsorbent.

To evaluate the differences in the adsorption kinetic rates, the pseudo-first-order, pseudo-second-order, intraparticle diffusion and Boyd models were used to fit the results.

The pseudo-first-order kinetic model is generally expressed as follows [39, 40]:

$$\log (q_e - q_t) = \log q_e - \frac{K}{2.303} t$$

Where q_e is the amount of Erythromycin adsorbed per unit mass of MWCNT at equilibrium (mg/g), q_t is the amount of Erythromycin adsorbed per unit mass of MWCNT at any time t (mg/g), t is the time (min), and K is the pseudo-first-order rate constant (1/min). The values of K and q_e were estimated from the slope and intercept of the linear plot of $\log (q_e - q_t)$ versus t (Fig 6a), and these values are listed in Table 2.

The pseudo-second-order kinetic model is given as follows [41, 42]:

$$\frac{t}{q_t} = \frac{1}{K_2 q_e^2} + \frac{1}{q_e} t$$

Where K_2 is the pseudo-second-order rate constant (g/mg.min) and $K_2 \cdot q_e^2 = h$ is the initial adsorption rate (mg/g.min). The values of K_2 and q_e were estimated from the slope and intercept of the linear plots of t/q_t versus t (Fig 6b), and the values are listed in Table 2.

The calculated q_e values for all the studied initial Erythromycin concentrations from the pseudo-first-order kinetic model differed appreciably from the experimental q_e values. However, in the pseudo-second-order kinetic model, the calculated q_e values were very close to the experimental q_e values for all the studied initial Erythromycin concentrations.

Furthermore, the obtained coefficient of determination (R^2) values of the pseudo-second-order kinetic model are higher than the obtained R^2 values of the pseudo-first-order kinetic model, indicating that the pseudo-second-order kinetic model better obeys the adsorption kinetic data than the pseudo-first-order kinetic model.

Intraparticle diffusion model

The intraparticle diffusion equation is given as [43, 44]:

$$q_t = K t^{0.5} + C$$

Where q_t is the amount of solute on the surface of the sorbent at time t (mg/g) and K is the intraparticle diffusion rate constant (mg/g.min^{1/2}). If intraparticle diffusion is the rate-limiting step in the adsorption of Erythromycin onto MWCNT, then the plot of q_t versus $t^{1/2}$ should be a straight line and pass through the origin. The deviation of the plot of q_t versus $t^{1/2}$ from linearity indicates that the rate-limiting step should be film diffusion controlled [45, 46]. It was observed from Figure 6 C that the plots consist of two linear portions: the first linear portion is due to film diffusion and the second is due to intraparticle diffusion. The straight line does not pass through the origin, therefore, intraparticle diffusion is not only the rate-limiting step, and film diffusion control may be involved in the adsorption process. The values of K and C were estimated from the slope and intercept of the plot of q_t versus $t^{1/2}$, and the constants of the intraparticle diffusion model are presented in Table 2 with R^2 values. The dual nature of the intraparticle diffusion plot (Fig 6 C) confirms the presence of both film and intraparticle diffusion. To anticipate the actual slowest step in the Erythromycin adsorption process, the obtained adsorption kinetic data were further analyzed using the Boyd kinetic model. The Boyd kinetic expression is given as [47, 48]:




$$F = \frac{q_t}{q_e} = 1 - \frac{6}{\pi^2} \exp(-Bt)$$

Equation can be modified and rearranged into the following form of the expression [49-51]:

$$B = -0.4977 - \ln(1-F) \quad F = \frac{q_t}{q_e}$$

Where q_e is the amount of adsorbate adsorbed at finite time (mg/g) and q_t represents the amount of Erythromycin adsorbed at any time t (min), F represents the fraction of solute adsorbed at any time t , and B is a mathematical function of F . The B values at different contact times can be calculated using equation above for various time intervals. The calculated B values were plotted against time t .

Figure 6d is used to identify whether the film diffusion or intraparticle diffusion controls the overall rate of the adsorption process. If the plots of $[(0.4977 - \ln(1-F))$ or B versus time t] are linear and pass through the origin, then the actual slowest step in the process of the adsorption of Erythromycin onto MWCNT is intraparticle diffusion. From Figures 6d, it was observed that the plots are linear but do not pass through the origin, which confirms that film diffusion mainly control the adsorption process.

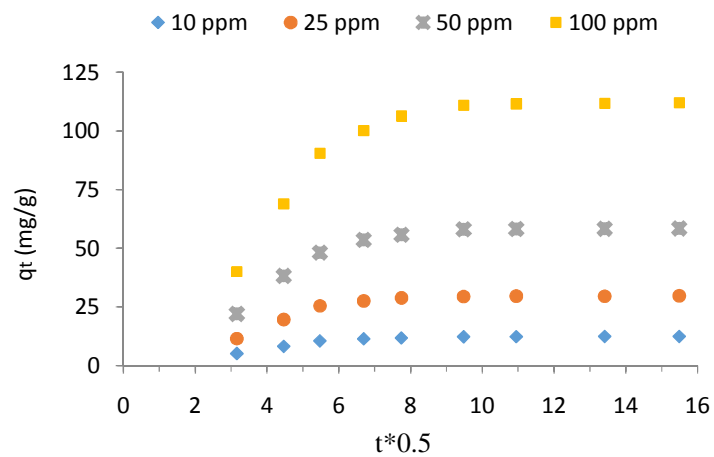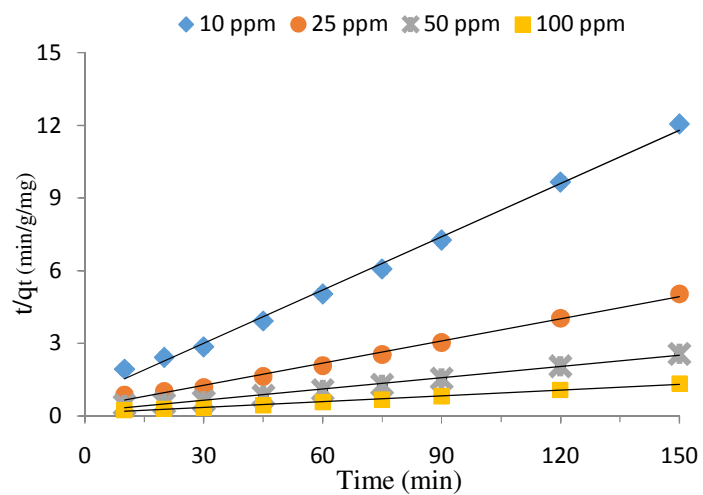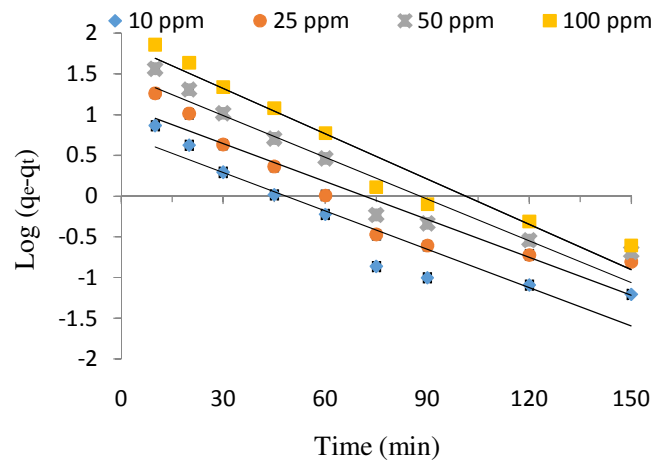

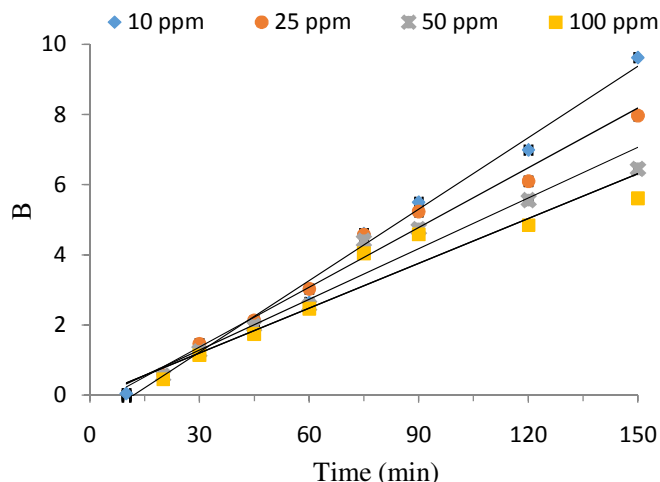


Fig. 6. Kinetic plots for the adsorption of Erythromycin onto MWCNT a: Pseudo-first order
b: Pseudo-second order C: Intraparticle diffusion d: Boyd model

Table 2: Kinetic parameters for the adsorption of Erythromycin onto MWCNT at various concentration

C_o (mg/L)	q_e (exp) mg/g	Pseudo-first order			Pseudo-second order			Intraparticle diffusion			Boyd
		K_1	q_e	R^2	K_2	q_e	R^2	K	C	R^2	R^2
10	12.43	0.024	4.91	0.892	0.0066	13.69	0.995	0.464	6.80	0.741	0.972
25	29.75	0.031	9.17	0.874	0.0026	33.33	0.993	1.13	16.11	0.756	0.956
25	58.44	0.034	25.16	0.909	0.0011	66.65	0.994	2.32	30.27	0.723	0.949
100	125.05	0.036	52.71	0.942	0.0004	142.8	0.993	4.73	54.33	0.784	0.962

4. CONCLUSION

The kinetics and thermodynamics of Erythromycin adsorption onto the MWCNT were studied. The Erythromycin adsorption of onto the MWCNT was rapid during the first 30 min and the equilibrium attained at 75 min. The kinetic of Erythromycin adsorption was described by applying the pseudo-first-order, pseudo-second-order, Intraparticle diffusion and Boyd models. The kinetic data for the adsorption process obeyed the pseudo-second-order kinetic model which it suggests that the adsorption process is chemisorption. The MWCNT studied showed the superb potential for the removal of Erythromycin from aqueous solution

ACKNOWLEDGEMENT

The authors are grateful of Zahedan University of Medical Sciences for supporting this study (Code Project: 97-8547).

REFERENCES

1. Balarak D, Mahdavi Y, Maleki A, Daraei H and Sadeghi S. Studies on the Removal of Amoxicillin by Single Walled Carbon Nanotubes. British Journal of Pharmaceutical Research. 2016;10(4): 1-9.
2. Putra EK, Pranowoa R, Sunarsob J, Indraswatia N, Ismadjia S. Performance of activated carbon and bentonite for adsorption of amoxicillin from wastewater: mechanisms, isotherms and kinetics. Water Res. 2009; 43, 2419-2430.

3. Adrianoa WS, Veredash V, Santanab CC, Gonçalves LRB. Adsorption of amoxicillin on chitosan beads: Kinetics, equilibrium and validation of finite bath models. *Biochemical Engineering Journal*. 2005; 27(2) ;132-37.
4. Balarak D, MahdaviY and Mostafapour FK. Application of Alumina-coated Carbon Nanotubes in Removal of Tetracycline from Aqueous Solution. *British Journal of Pharmaceutical Research*.2016; 12(1): 1-11.
5. Chen WR, Huang CH. Adsorption and transformation of tetracycline antibiotics with aluminum oxide. *Chemosphere*. 2010; 79, 779–785.
6. Xu L, Pan J, Dai J, Li X, Hang H, Cao Z, Yan Y. Preparation of thermal-responsive magnetic molecularly imprinted polymers for selective removal of antibiotics from aqueous solution. *Journal of Hazardous Materials*. 2012; 233-234;48-56.
7. Alexy R, Kumpel T, Kummerer K. Assessment of degradation of 18 antibiotics in the closed bottle test. *Chemosphere*. 2004 ; 57, 505–512.
8. Balarak D, Azarpira H, Mostafapour FK. Study of the Adsorption Mechanisms of Cephalexin on to AzollaFiliculoides. *Der Pharma Chemica*, 2016, 8(10):114-121
9. Balarak D, Mostafapour FK, Joghataei A. Experimental and Kinetic Studies on Penicillin G Adsorption by Lemna minor. *British Journal of Pharmaceutical Research*. 2016; 9(5): 1-10.
10. Choi KJ, Kim SG, Kim SH. Removal of antibiotics by coagulation and granular activated carbon filtration. *J. Hazard. Mater*. 2008; 151;38–43.
11. Fatta-Kassinos D, Meric S, Nikolau A. Pharmaceutical residues in environmental waters and wastewater: current state of knowledge and future research, *Anal. Bioanal. Chem*. 2011; 399; 251-275.
12. Maria HL, Ribeiro E, Isabel AC. Modelling the adsorption kinetics of erythromycin onto neutral and anionic resins. *Bioprocess Biosyst Eng*. 2003; 26: 49–55.
13. Balarak D, Mostafapour FK, Bazrafshan E, Saleh, TA. Studies on the adsorption of amoxicillin on multi-wall carbon nanotubes. *Water science and technology*. 2017; 75(7); 1599-1606
14. Balarak D, Mostafapour FK. Batch Equilibrium, Kinetics and Thermodynamics Study of Sulfamethoxazole Antibiotics Onto Azolla filiculoides as a Novel Biosorbent. *British journal of pharmaceutical research*. 2017;13(2); 1-11.
15. Balarak D, Mostafapour FK, Khatibi AD. Nonlinear Isotherms and Kinetics and Application Error Functions for Adsorption of Tetracycline on Lemna Minor. *British journal of pharmaceutical research*. 2018;23(2); 1-11.
16. Yu F, Li Y, Han S, Jie Ma J. Adsorptive removal of antibiotics from aqueous solution using carbon Materials. *Chemosphere*. 2016;153;365–385.
17. Aksu Z, Tunc O. Application of biosorption for Penicillin G removal: Comparison with activated carbon. *Process Biochemistry*. 2005;40(2):831-47.
18. Balarak, D, Joghataei A, Mostafapour FK. Ciprofloxacin Antibiotics Removal from Effluent Using Heat-acid Activated Red Mud. *British journal of pharmaceutical research*. 2017; 20(5); 1-11.
19. Balarak D, Mostafapour FK, Azarpira H. kinetic and Equilibrium Studies of Sorption of Metronidazole Using Graphene Oxide. *British journal of pharmaceutical research*. 2017; 19 (4); 1-10.
20. Ji L, ChenW, Duan L and Zhu D. Mechanisms for strong adsorption of tetracycline to carbon nanotubes: A comparative study using activated carbon and graphite as adsorbents. *Environ. Sci. Technol*. 2009,43 (7), 2322–27.
21. Balarak D, Mostafapour FK, Joghtaei A. Thermodynamic Analysis for Adsorption of Amoxicillin onto Magnetic Carbon Nanotubes. *British journal of pharmaceutical research*. 2017; 16 (6); 1-10.
22. Azarpira H, Mahdavi Y, Khaleghi O, Balarak D. Thermodynamic studies on the removal of metronidazole antibiotic by multi-walled carbon nanotubes. *Der Pharmacia Lettre*. 2016; 8(11):107-13.
23. Abdel-Rahman LH, Abu-Dief AM, Abd- El Sayed MA, Megalea Zikry M. Nano Sized Moringa oleifera an Effective Strategy for Pb(II) ions Removal from Aqueous Solution, *Chemistry and Materials Research*, 2016, 8, 1-7.
24. Dutta M, Dutta NN, Bhattachary KG. Aqueous phase adsorption of certain beta-lactam antibiotics onto polymeric resins and activated carbon. *Separation and Purification Technology*.1999;16(3);213-24.

25. Peterson JW, Petrasky LJ, Seymoure MD, Burkhardt RS, Schuilinga AB. Adsorption and breakdown of penicillin antibiotic in the presence of titanium oxide nanoparticles in water. *Chemosphere*. 2012;87(8); 911-7.
26. Ghauch A, Tuqan A, Assi HA: Elimination of amoxicillin and ampicillin by micro scale and nano scale iron particles. *Environ Pollut*. 2009;157:1626–1635.
27. Balarak D, Mostafapour FK, Akbari, H. Adsorption of Amoxicillin Antibiotic from Pharmaceutical Wastewater by Activated Carbon Prepared from *Azolla filiculoides*. *British journal of pharmaceutical research*. 2017; 18(3); 1-10.
28. Balarak D, Azarpira H. Photocatalytic degradation of sulfamethoxazole in water: investigation of the effect of operational parameters. *International Journal of Chem Tech Research*. 2016; 9(12):731-8.
29. Balarak D, Mostafapour FK, Azarpira H. Adsorption Kinetics and Equilibrium of Ciprofloxacin from Aqueous Solutions Using *Corylus avellana* (Hazelnut) Activated Carbon. *British journal of pharmaceutical research*. 2016; 13 (3); 1-10.
30. Erşan M, Bağd E. Investigation of kinetic and thermodynamic characteristics of removal of tetracycline with sponge like, tannin based cryogels. *Colloids and Surfaces B: Biointerfaces*. 2013;104;75-82.
31. Banerjee SS, Chen DH. Fast removal of copper ions by gum arabic modified magnetic nano-adsorbent, *J. Hazard Mater*. 2007;147;792–799.
32. Qu S, Wang J, Kong J, Yang P, Chen G. Magnetic loading of carbon nanotube/nano-Fe₃O₄ composite for electrochemical sensing, *Talanta*. 2007; 71;1096–102.
33. Wu C, Adsorption of reactive dye onto carbon nanotubes: equilibrium, kinetics and thermodynamics, *J. Hazard Mater*. 2007;144;93–100.
34. Balarak D, Mostafapour FK. Batch Equilibrium, Kinetics and Thermodynamics Study of Sulfamethoxazole Antibiotics Onto *Azolla filiculoides* as a Novel Biosorbent. *British journal of pharmaceutical research*. 2016; 13 (2); 1-10.
35. Balarak D, Mostafapour FK, Azarpira H. Langmuir, Freundlich, Temkin and Dubinin-radushkevich Isotherms Studies of Equilibrium Sorption of Ampicillin onto Montmorillonite Nanoparticles. *British journal of pharmaceutical research*. 2016; 20 (2); 1-10.
36. Abdel-Rahman LH, El-Khatib RM, Nassr LAE, Abu-Dief AM. Synthesis, physicochemical studies, embryos toxicity and DNA interaction of some new Iron(II) Schiff base amino acid complexes. *Journal of Molecular Structure*. 2013; 1040;9–18.
37. Abdel-Rahman LH, Abu-Dief AM, Moustafa H, Kamel Hamdan S. Ni(II) and Cu(II) complexes with ONNO asymmetric tetradentate Schiff base ligand: synthesis, spectroscopic characterization, theoretical calculations, DNA interaction and antimicrobial studies, *Appl. Organometal. Chem*. 2017; 31; 3555.
38. Abdel-Rahman LH, Abu-Dief AM, El-Khatib RM, Abdel-Fatah SM, Adam AM, Ibrahim EMM, Sonochemical synthesis, structural inspection and semiconductor behavior of three new nano sized Cu(II), Co(II) and Ni(II) chelates based on tri- dentate NOO imine ligand as precursors for metal oxides. *Appl Organo metal Chem*. 2018; 3; 41-74.
39. Abdel-Rahman LH, Al-Farhan BSF, Abu-Dief AM and Zikry MM, Removal of Toxic Pb(II) Ions from Aqueous Solution by Nano Sized Flamboyant Pod (*Delonix regia*). *Ahives in Chemical Research*. 2016; 1; 1-10.
40. Mohamed WS, Abu-Dief AM, Synthesis, characterization and photocatalysis enhancement of Eu₂O₃-ZnO mixed oxide nanoparticles. *Journal of Physics and Chemistry of Solids*. 2018; 116; 375–385
41. Yang N, Zhu S, Zhang D, Xu S. Synthesis and properties of magnetic Fe₃O₄-activated carbon nanocomposite particles for dye removal. *Mater. Lett*. 2008; 62;645–47.
42. Peng H, Pana B, Wu M, Ran Liu R, Zhanga D, Wu D, Xing B. Adsorption of ofloxacin on carbon nanotubes: Solubility, pH and cosolvent effects. *Journal of Hazardous Materials*. 2012;211-212;342-48.
43. Chang PH, Li Z, Jean JS, Jiang WT, Wang CJ, Lin KH. Adsorption of tetracycline on 2:1 layered non-swelling clay mineral illite. *Appl. Clay Sci*. 2012; 67;158–163.
44. Balarak D, Mostafapour FK, Joghataei A. Kinetics and mechanism of red mud in adsorption of ciprofloxacin in aqueous solution. *Bioscience biotechnology research communications*. 2017; 10(1);

241-248.

45. Balarak D, Mostafapour F K, Joghataei A. Biosorption of amoxicillin from contaminated water onto palm bark biomass. *International journal of life science and pharma research*. 2017;7(1);9-16
46. Upadhyayula VKK, Deng S , Mitchell MC, Smith GF. Application of carbon nanotube technology for removal of contaminants in drinking water: A review. *Science of the Total Environment*. 2009; 408; 1–13.
47. Rostamian R, Behnejad H. A comparative adsorption study of sulfamethoxazole onto graphene and graphene oxide nanosheets through equilibrium, kinetic and thermodynamic modeling. *Process Safety and Environmental Protection*. 2016;102;20-29.
48. Khaled A, Nem AE, El-Sikaily A, Abdelwahab O. Removal of Direct N Blue- 106 from artificial textile dye effluent using activated carbon from orange peel: adsorption isotherm and kinetic studies, *J. Hazard. Mater.* 2009; 165 ;100–110.
49. Gao Y, Li Y, Zhang L, Huang H, Hu J, Shah SM, Su X. Adsorption and removal of tetracycline antibiotics from aqueous solution by graphene oxide, *J. Colloid. Interface Sci.* 2012; 368; 540–546.
50. Ma W, Ya FQ, Han M, Wang R. Characteristics of equilibrium, kinetics studies for adsorption of fluoride on magnetic-chitosan particle, *J. Hazard Mater.* 2007;143;296–302.
51. Gao J and Pedersen JA. Adsorption of Sulfonamide Antimicrobial Agents to Clay Minerals. *Environ. Sci. Technol.* 2005, 39(24). 9509-16.