

1  
2 **Kinetics Properties of Pine Sawdust and Municipal Solid Waste - A Case Study of Arusha &**  
3 **Kilimanjaro – Tanzania**  
4

5  
6 **Abstract**

7 The main economic activity in most of developing countries includes the exploitation of natural  
8 resources and agriculture. The wastes generated from these sectors are such as sawdust and  
9 municipal solid waste. The main purpose of this paper is to determine and compare the kinetic  
10 properties of these wastes. The kinetics analysis shows that the activation energy varies with  
11 temperature. The analysis of pine sawdust shows that it has activation energy ( $E_a$ ) values of 26.19  
12 kJ/mol., 87.46 kJ/mol. and 54.46 kJ/mol. with respective temperature ranges between 350 – 400K,  
13 550 – 650K and 700 800K. Municipal solid waste has activation energy between 72.91kJ/mol. and  
14 139.1 kJ/mol. with temperature ranges between 700 – 900K and 500 – 600K respectively. The  
15 estimated value of pre-exponential factor for pine sawdust has the values of  $2.46 \times 10^4$ ,  $1.6 \times 10^{10}$   
16 and  $5.32 \times 10^{16}$  ( $s^{-1}$ ) with temperature ranges between 350 – 400K, 550 – 650K and 700 800K  
17 respectively. Municipal solid waste has the values of  $3.01 \times 10^{12}$  and  $7.31 \times 10^3$  ( $s^{-1}$ ) with a  
18 temperature range of 500 – 600K and 700 – 900K respectively.  
19

20 **Keywords:** Municipal solid waste, Pine sawdust, Kinetics, TGA  
21

22 **1. INTRODUCTION**

23 The sustainable economic development of any country is usually accompanied with energy demand  
24 increases and environment degradation challenges (Wolfram *et al.*, 2012; Kichonge *et al.*, 2014;  
25 Ahmed *et al.*, 2017). As economic sectors grows the energy demand and waste generation in cities  
26 rises primarily influenced by population growth, changing life styles and thus rapid urbanization  
27 (Tsamba *et al.*, 2006; Chiemchaisri and Visvanathan, 2008; Gentil *et al.*, 2009; Omari *et al.*, 2014).  
28 Inappropriate waste management strategies and insufficient energy supply contributes to poor life quality  
29 in cities (Kuo *et al.*, 2008; Johari *et al.*, 2012; Kichonge *et al.*, 2015) as a result of uncontrolled  
30 greenhouse gases (GHGs) emission to the atmosphere among others (Noor *et al.*, 2013). Municipal solid  
31 waste (MSW) uncontrolled burning results in emissions of gases such as methane and carbon dioxide  
32 and therefore considered as among major climate change contributors (Chiemchaisri and Visvanathan,  
33 2008; Kothari *et al.*, 2010; Udomsri *et al.*, 2011). Then again, the emissions of GHGs such as carbon  
34 dioxide, methane and nitrous oxide from agriculture activities are considered to be among climate  
35 change contributors (Cole *et al.*, 1997; Smith *et al.*, 2007).  
36

37 The primary sources of energy for many years have been from fossil fuels, which are fast depleted and  
38 contributed to the global warming (Ryu, 2010; Shahsavari and Akbari, 2018). There is a need for a  
39 sustainable source of renewable energy to replace fossil fuels. The biogenic fraction of municipal  
40 solid waste and forest waste are renewable in nature and therefore they can be used mitigate energy  
41 and environmental challenges (Mohammed *et al.*, 2013). Waste to energy is among approaches in  
42 waste management while mitigating energy challenges (Barbieri *et al.*, 2016). Renewable waste  
43 materials from MSW and agriculture activities such as pine saw dust are convertible to useful energy  
44 forms through waste to energy routes for sustainable development. Compared to fossil fuels pine sawdust  
45 and MSW due to their nature can reduces equivalent  $CO_2$ ,  $SO_2$  and  $NO_x$  emissions (Baxter, 2005;  
46 Shahsavari and Akbari, 2018).  
47

48 The abundant pine sawdust and municipal solid wastes and their renewable nature are encouraging  
49 their utilization as the source of sustainable renewable energy (Pandey *et al.*, 2016b). Pine sawdust  
50 and municipal solid wastes need to be processed so as to upgrade its fuel quality for energy recovery  
51 (Chaula *et al.*, 2014b). There are many ways of energy recovery from pine sawdust and municipal  
52 wastes, but the common one being physical treatment such as making pellets, thermal treatment such  
53 as combustion, pyrolysis, and gasification (Chen *et al.*, 2016). Biological treatment such as  
54 fermentation and anaerobic digestion (Sharholly *et al.*, 2008). The municipal solid waste contains a  
55 big portion of biomass materials such as food, wood, and paper (Pandey *et al.*, 2016a). The  
56 knowledge of thermal degradation is essential for predicting the pyrolysis behavior of municipal

57 solid waste and pine sawdust materials (Johari *et al.*, 2012). The characterization makes easier to  
58 optimize their utilization and gives essential information in designing the suitable reactor for their  
59 disposal (Sonobe and Worasuwannarak, 2008; Clarke and Preto, 2011). Thermal degradation of pine  
60 sawdust and municipal solid waste pose a big challenge due to their nature and composition  
61 (Belgiorno *et al.*, 2003). The chemical reactions that take place during their degradation and  
62 chemical kinetics used to estimate the potentiality for energy recovery (Chaula *et al.*, 2014a).  
63 Thermal degradation values such as activation energy, frequency factor, rate of reaction, calorific values,  
64 differential scanning calorimetry and differential thermal gravimetric can be determined by using  
65 thermogravimetric analysis (TGA) (Chen *et al.*, 2014; Mhilu, 2014; Mishra and Mohanty, 2018). The  
66 purpose of this study was to determine and analyses the kinetics properties comparisons of pine sawdust  
67 and municipal solid waste using TGA and therefore to provide a theoretical basis for their utilization.  
68

## 69 **2. MATERIAL AND METHODS**

### 70 **2.1. Material Sampling and Collection**

71 Municipal solid waste and the pine sawdust collected from various saw mills in Arusha & Kilimanjaro  
72 were used. Different equipment and standard test methods were adopted in order to determine and  
73 analyze thermal degradation. The airtight polythine bags were used for quality assurance and safety of  
74 samples transport from source to laboratory for analysis.

### 75 **2.2. Municipal waste collection**

76 The sampling of municipal solid waste material was based on ASTM D5231-03. The method for  
77 random sampling for determination of the composition of unprocessed municipal solid waste  
78 (ASTM, 2003; Gidaracos *et al.*, 2006). The waste was randomly collected and categorized to plastic,  
79 paper, food, and non-combustibles. The combustible components were collected for laboratory  
80 analysis.

### 81 **2.3. Pine sawdust collection**

82 The pine sawdust samples obtained from sawmill were natural dried and collected for laboratory  
83 analysis.

### 84 **2.4. Thermal Degradation Analysis Study**

85 The experiments for the pyrolysis of wastes were performed by using thermo-gravimetric analyzer  
86 type NETZSCH STA 409 PC L<sub>uxx</sub>. Then samples collected as per municipal waste and pine sawdust  
87 sampling paragraphs above were grounded to small particles of 1mm and oven dried at 378K  
88 constant weight. Then a sample of 30±0.1 mg of wastes with an average particle size less than 1mm  
89 was loaded to the crucible and subjected into the furnace and heated. These samples mass are small  
90 and therefore it is assumed that the thermal degradation within the sample is negligible (Dirion *et al.*, 2008).

91 The thermal gravimetric analyzer connected to PC installed with proteus software for data  
92 acquisition, storage and analysis. The thermal gravimetric analyzer is used to measure the quantity  
93 of mass change due to physical and chemical reactions; it is combined the heat flux differential  
94 scanning calorimetry which determines the physical and chemical reactions associated with thermal  
95 effect. The profile curves of TG, DTG and DSC were obtained from Proteus software (Wilson *et al.*,  
96 2011).  
97

#### 98 **2.4.1. Municipal solid wastes thermal degradation analysis**

99 The municipal solid waste samples and subjected to heat at temperature ranges vary from 308 to  
100 1273K and heating rate of 10K/min. The calculated thermo-gravimetric from Proteus software was  
101 obtained and recorded.

#### 102 **2.4.2. Thermal degradation analysis of pine sawdust**

103 The pine sawdust samples were subjected to heat at temperature ranges from 308 to 973K with a  
104 heating rate of 10K/min. The calculated thermo-gravimetric output from Proteus software was  
105 obtained and recorded.

### 106 **2.5. Kinetic parameters analysis**

107 The method deployed to determine Kinetic parameter was Coasts-Red fern methods equation (1). It  
108 is used as a standard method for studying the thermal degradation of pine sawdust and municipal  
109 solid waste under non-isothermal condition (Amutio *et al.*, 2012; Farrokh *et al.*, 2019). The Coasts-  
110 Red fern method used to calculate the kinetic parameters of first-order reaction (Coats and Redfern,  
111 1964; Tsamba *et al.*, 2006).

112 
$$\ln\left[\frac{-\ln(1-x)}{T^2}\right] = \left[\frac{AR}{\beta E_a}\left(1 - \frac{2RT}{E_a}\right)\right] - \frac{E_a}{RT} \quad (1)$$

113 Using the known heating rate, the line graph of  $\ln\left[\frac{-\ln(1-x)}{T^2}\right]$  versus  $1/T$  understudied  
 114 material will be a straight-line graph. The slope and intercept of the line graphs were used to  
 115 calculate the kinetic parameters (Lai *et al.*, 2011; Tan *et al.*, 2019).

116 Since the value of  $\frac{2RT}{E_a} \ll 1$  that can be neglected, the interception on the vertical axis is  $\left(\frac{AR}{\beta E_a}\right)$

117 and the slope line is  $\frac{E_a}{R}$  can be used to determine the values of  $E_a$  and  $A$ .

118 The constant heating rate ( $\beta$ ) is expressed as shown in Equation 2.

119 
$$\beta = dT/dt \quad (2)$$

120 The rate constant for the process is expressed by Arrhenius Equation 3.

121 
$$k = A \exp\left(-\frac{E_a}{RT}\right) \quad (3)$$

122 Where:  $k$  is the rate constant which depends on the temperature

123  $A$  is the pre-exponential factor ( $S^{-1}$ )

124  $E_a$  is the activation energy ( $kJ/mol$ )

125  $R$  is the universal gas constant ( $8.3142 kJmol^{-1} K^{-1}$ ) and

126  $T$  is the temperature ( $K$ )

127 
$$\frac{dx}{dt} = k f(x) \quad (4)$$

128  $f(x)$  Algebraic function depending on reaction mechanism

129 
$$\frac{dx}{dt} = Af(x) \exp\left(-\frac{E_a}{RT}\right) \quad (5)$$

130 Degree of conversion  $x$

131 
$$x = (w_0 - w_t) / (w_0 - w_\infty) \quad (6)$$

132 Where:


133  $w_0$  Initial mass

134  $w_t$  The mass remaining at time  $t$

135  $w_\infty$  The final mass remaining

136

137 **3. RESULTS AND DISCUSSION**  
 138 **3.1. TG Analysis of Municipal Solid Waste and Pine Sawdust**

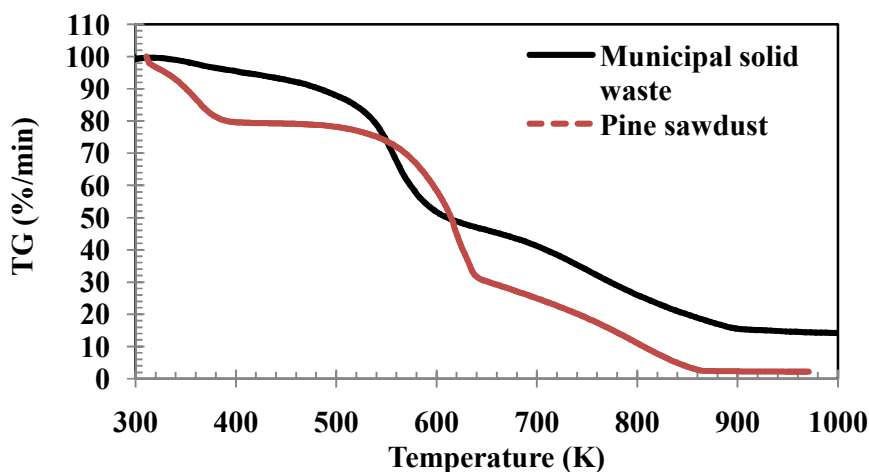


139  
140  
141 **Figure 1: TG Curves of Municipal solid waste and Pine sawdust**

142  
143 **Table 1: TG results of Municipal solid waste and pine sawdust**

S/N	Material	Moisture release	Volatile release	Remaining Char& Ash
1	Municipal solid waste	3.6	80.8	15.6
2	Pine sawdust	18.9	77.5	3.6

144  
145 The thermo-gravimetric analysis results were shown in Fig 1 and Table 1. The value of ash  
146 remaining in pine sawdust is much less compared to municipal solid waste. The big amount of  
147 moisture released at 378K from pine sawdust (18%) shows that there are much moisture contents in  
148 pine sawdust than in municipal solid waste. There is also slightly more volatiles in municipal solid  
149 waste than in pine sawdust. The value of ash remaining is higher in municipal solid waste than in  
150 pine sawdust shows that there are many mineral components in municipal solid waste than in pine  
151 sawdust (Quina *et al.*, 2018).


152 **3.2. DTG analysis of municipal solid waste and pine sawdust**

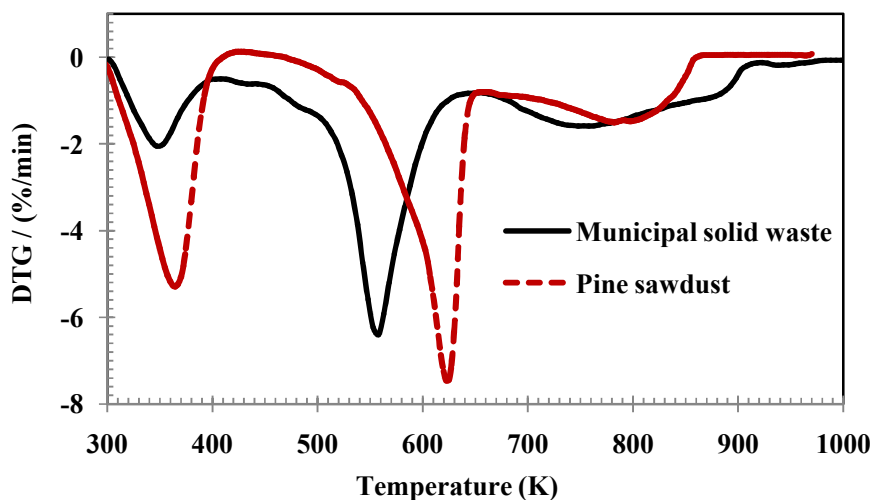

153  
154 **Figure 2: DTG of municipal solid waste and pine sawdust**  
155

156 Fig 2 shows the derivative of thermo-gravimetric analysis (DTG), for municipal solid waste and  
157 pine sawdust. The municipal solid waste curve shows that the degradation derived in four shoulders.  
158 The first shoulder is the degradation of moisture, this is ranging from 303K to 423K, and the second  
159 shoulder is the lignocellulose degradation which ranges between 423 and 643K. The third shoulder  
160 ranges between 643 and 913K shows the degradation of plastics and hemicellulose materials (Quina  
161 *et al.*, 2018). There is very small char pyrolysis in pine sawdust curve since it has a very little char  
162 remaining in the reaction, Fig 1 and Fig 2 (Lai *et al.*, 2011). The degradation of plastic and  
163 hemicellulose materials are overlapping in municipal solid waste degradation while the degradation  
164 of hemicellulose in pine sawdust is clearly defined in Fig 2. The char pyrolysis falls in 4<sup>th</sup> shoulder  
165 ranges between 913 and 1273K.  
166

### 167 3.3. DSC Analysis of Municipal Solid Waste and Pine Sawdust

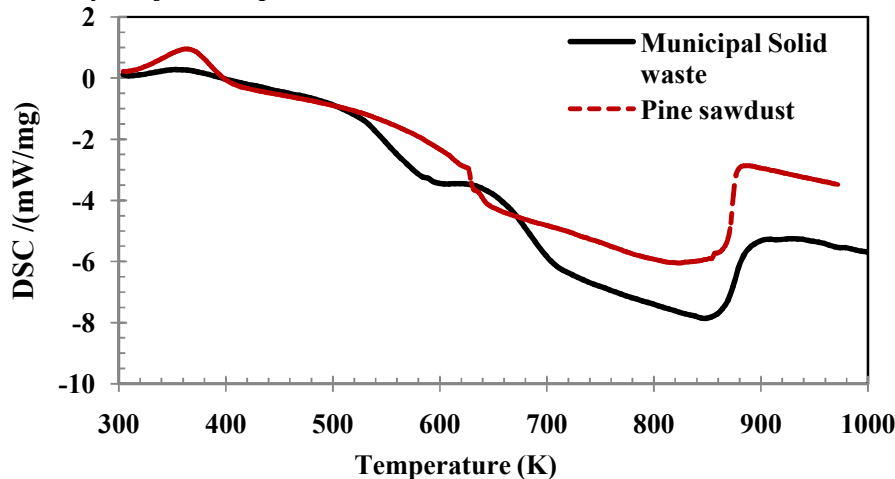


168 **Figure 3:** DSC from Municipal Solid Waste and Pine Sawdust  
169  
170

171 Figure 3 shows the differential scanning calorimetry curves. All curves show that there are  
172 endothermic reactions during its initial stage of degradation. The temperature range between 300  
173 and 370K, this is due to the release of moisture. The pine sawdust curve is higher than a municipal  
174 solid waste curve. The value of this moisture is clearly seen in the TG and DTG curves (Fig 1 and  
175 Fig 2). The energy used to release moisture from pine sawdust is higher than that used in municipal  
176 solid waste. The structure of pine sawdust is so that the moisture is entrained in its cell walls and for  
177 that case, it requires more energy to remove moisture from pine sawdust than in municipal solid  
178 waste (Wilson *et al.*, 2011). An energy release result due to differential scanning calorimetry (DSC)  
179 of municipal solid waste has energy quantity ranging from 7.6 to 8.5MJ/kg. Compared to the energy  
180 found from bomb calorimetry about 12MJ/kg. The energy amount found in DSC is low. The energy  
181 found during bomb calorimetry is the energy determined from dry MSW pellets. The energy found  
182 during DSC is the energy remaining after drying MSW. The energy to dry MSW that make the  
183 difference between the two. The energy released due to DSC of pine sawdust has the energy value of  
184 15.1 MJ/kg.  
185

186 **3.4. Kinetic parameters of municipal solid waste**

187 The value from the TGA curve of MSW obtained and put into Coats Red-fern method give the value  
 188 as shown in Fig 4.

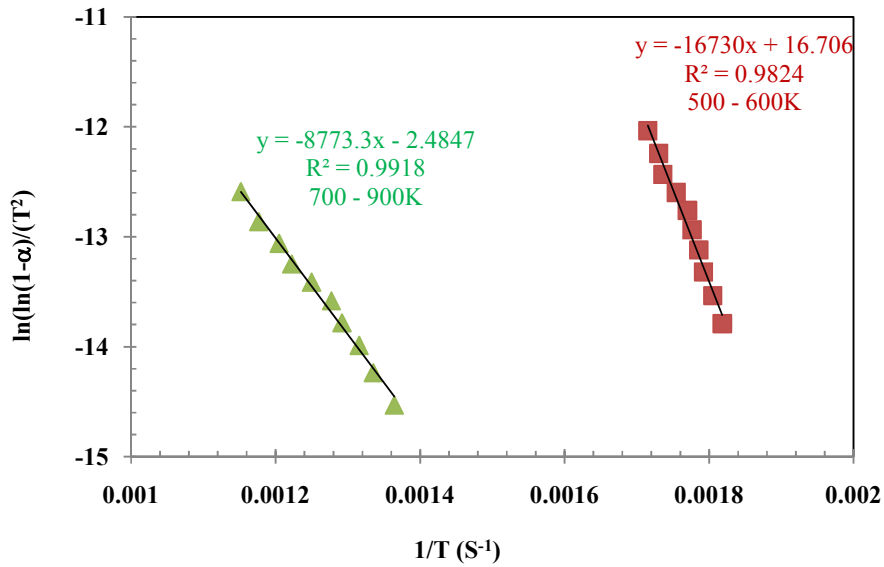


189 **Figure 4:** Determination of kinetic parameter of Municipal solid waste

189  
 190  
 191

192 The kinetic parameters of municipal solid waste are shown in 2 curves. The kinetic parameter at  
 193 high-temperature peak and at the low-temperature peak as shown in Fig 4 and Table 2. The kinetic  
 194 parameter graphs show the values of Pre-exponential factor (A) for municipal solid waste as  $3.01 \times 10^{12}$   
 195 and  $7.31 \times 10^3$  (S<sup>-1</sup>) for low and high temperature respectively. The value of  $E_a$  for municipal  
 196 solid waste is 72.91 and 139.1 kJ/mol. for low and high temperature respectively.

197 **3.5. Kinetic parameters of pine sawdust**

198 The value from the TGA curve of pine sawdust obtained and insert into Coats Redfern method gives  
 199 the value as shown in fig. 5

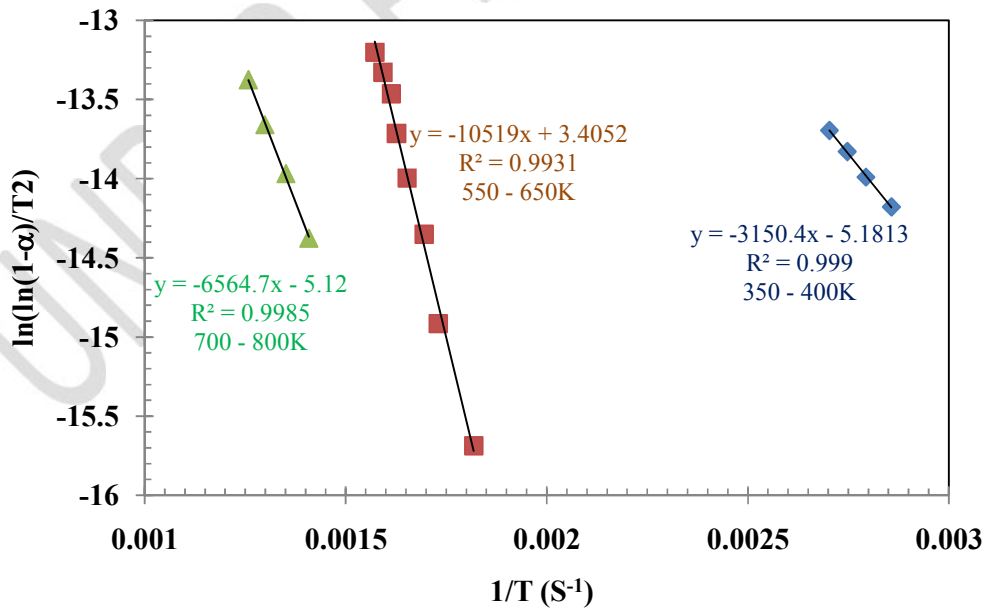

200 **Figure 5:** Determination of the kinetic parameter of pine sawdust

200  
 201  
 202  
 203  
 204

203 The pine sawdust kinetic parameters have shown in Fig 5 in three curves, the degradation of  
 204 hemicellulose at low-temperature peak and of cellulose at high-temperature peak. The results

205 tabulated in Table 2 show that the activation energy  $E_a$  ranging from 26.19 to 87.46 kJ/mol. The  
 206 value of pre-exponential factor increases from  $2.46 \times 10^4$ ,  $1.6 \times 10^{10}$  and  $5.32 \times 10^{16}$  ( $S^{-1}$ ) with a  
 207 respective increase in the temperature range of 350 – 400K, 550 – 600K and 700 – 800K.

208  
 209 **Table 2:** Activation energy and Pre-exponential factor of municipal solid waste and pine  
 210 sawdust

Type of waste	Temperature (K)	Activation energy (kJ/mole)	Pre-exponential factor ( $s^{-1}$ )
Municipal solid waste	500 - 600	139.1	$3.01 \times 10^{12}$
	700 - 900	72.91	$7.31 \times 10^3$
Pine sawdust	350 – 400	26.19	$2.46 \times 10^4$
	550 – 600	87.46	$1.6 \times 10^{10}$
	700 – 800	54.58	$5.32 \times 10^{16}$

211

#### 212 4. CONCLUSION

213

The followings are the conclusions of the findings which determined and compared the kinetic properties of MSW and pine saw dust.

214

215

- This paper finds related to municipal solid waste and biomass waste characterization from Arusha and Kilimanjaro respectively.
- There is a potential for energy recovery from the municipal solid waste and pine sawdust.
- The energy recovery from dry MSW is 10.6 MJ/kg while energy recovery from dry pine sawdust is 15.1 MJ/kg.
- DSC shows that at the beginning the reactions are endothermic due to the release of moisture from the samples and thereafter moisture released the reactions undergo exothermic.

216

217

218

219

220

221

222

223

224

#### 225 REFERENCES

226

227

Ahmed, K., Rehman, M.U. and Ozturk, I. (2017). What drives carbon dioxide emissions in the long-run? Evidence from selected South Asian Countries. *Renewable and Sustainable Energy Reviews*. **70**(1): 1142-1153.

230

Amutio, M., Lopez, G., Aguado, R., Artetxe, M., Bilbao, J. and Olazar, M. (2012). Kinetic study of lignocellulosic biomass oxidative pyrolysis. *Fuel*. **95**(1): 305-311.

232

ASTM (2003). ASTM D5231-92, Standard Test Method for the Determination of the Composition of Unprocessed Municipal Solid Waste. ASTM International, West Conshohocken, PA.

234

Barbieri, L., Andreola, F., Taurino, R., Ponzoni, C., Leonelli, C., Lancellotti, I., Arancon, R.A.D., Lin, C.S.K., Chan, K.M. and Kwan, T.H. (2016). Waste Management and Valorization Alternative Technologies, in: RADA, E. C. (Ed.). Apple Academic Press, Waretown, New Jersey 08758 USA.

236

Baxter, L. (2005). Biomass-coal co-combustion: opportunity for affordable renewable energy. *Fuel*. **84**(10): 1295-1302.

238

Belgiorno, V., De Feo, G., Della Rocca, C. and Napoli, R. (2003). Energy from gasification of solid wastes. *Waste management*. **23**(1): 1-15.

240

Chaula, Z., Said, M. and John, G. (2014a). Thermal Characterization of Pine Sawdust as Energy Source Feedstock. *Journal of Energy Technologies and Policy*. **4**(4): 57-64.

242

Chaula, Z., Said, M., John, G., Manyele, S. and Mhilu, C. (2014b). Modelling the Suitability of Pine Sawdust for Energy Production via Biomass Steam Explosion. *Smart Grid and Renewable Energy*. **5**(1): 1-7.

244

Chen, D., Zhou, J. and Zhang, Q. (2014). Effects of heating rate on slow pyrolysis behavior, kinetic parameters and products properties of moso bamboo. *Bioresour technology*. **169**(1): 313-319.

247

248

- 249 Chen, P., Xie, Q., Addy, M., Zhou, W., Liu, Y., Wang, Y., Cheng, Y., Li, K. and Ruan, R. (2016). Utilization of  
 250 municipal solid and liquid wastes for bioenergy and bioproducts production. *Bioresource*  
 251 *technology*. **215**(1): 163-172.
- 252 Chiemchaisri, C. and Visvanathan, C. (2008). Greenhouse gas emission potential of the municipal solid  
 253 waste disposal sites in Thailand. *Journal of the Air & Waste Management Association*. **58**(5):  
 254 629-635.
- 255 Clarke, S. and Preto, F. (2011). Biomass burn characteristics. Ministry of Agriculture, Food and Rural  
 256 Affairspp.
- 257 Coats, A. and Redfern, J. (1964). Kinetic parameters from thermogravimetric data. *Nature*. **201**(4914):  
 258 68-69.
- 259 Cole, C., Duxbury, J., Freney, J., Heinemeyer, O., Minami, K., Mosier, A., Paustian, K., Rosenberg, N.,  
 260 Sampson, N. and Sauerbeck, D. (1997). Global estimates of potential mitigation of greenhouse  
 261 gas emissions by agriculture. *Nutrient cycling in Agroecosystems*. **49**(1-3): 221-228.
- 262 Dirion, J.-L., Reverte, C. and Cabassud, M. (2008). Kinetic parameter estimation from TGA: Optimal  
 263 design of TGA experiments. *Chemical Engineering Research and Design*. **86**(6): 618-625.
- 264 Farrokh, N.T., Suopajarvi, H., Sulasalmi, P. and Fabritius, T. (2019). A thermogravimetric analysis of  
 265 lignin char combustion. *Energy Procedia*. **158**(1): 1241-1248.
- 266 Gentil, E., Clavreul, J. and Christensen, T.H. (2009). Global warming factor of municipal solid waste  
 267 management in Europe. *Waste Management & Research*. **27**(9): 850-860.
- 268 Gidarakos, E., Havas, G. and Ntzamilis, P. (2006). Municipal solid waste composition determination  
 269 supporting the integrated solid waste management system in the island of Crete. *Waste*  
 270 *management*. **26**(6): 668-679.
- 271 Johari, A., Hashim, H., Mat, R., Alias, H., Hassim, M. and Rozzainee, M. (2012). Generalization,  
 272 formulation and heat contents of simulated MSW with high moisture content. *Journal of*  
 273 *Engineering Science and Technology*. **7**(6): 701-710.
- 274 Kichonge, B., John, G.R., Mkilaha, I. and Sameer, H. (2014). Modelling of future energy demand for  
 275 Tanzania. *Journal of Energy Technologies and Policy*. **4**(7): 16-31.
- 276 Kichonge, B., John, G.R. and Mkilaha, I.S. (2015). Modelling energy supply options for electricity  
 277 generations in Tanzania. *Journal of Energy in Southern Africa*. **26**(3): 41-57.
- 278 Kothari, R., Tyagi, V. and Pathak, A. (2010). Waste-to-energy: A way from renewable energy sources to  
 279 sustainable development. *Renewable and sustainable energy reviews*. **14**(9): 3164-3170.
- 280 Kuo, J.H., Tseng, H.H., Rao, P.S. and Wey, M.Y. (2008). The prospect and development of incinerators  
 281 for municipal solid waste treatment and characteristics of their pollutants in Taiwan. *Applied*  
 282 *Thermal Engineering*. **28**(17): 2305-2314.
- 283 Lai, Z., Ma, X., Tang, Y. and Lin, H. (2011). A study on municipal solid waste (MSW) combustion in N<sub>2</sub>/O<sub>2</sub>  
 284 and CO<sub>2</sub>/O<sub>2</sub> atmosphere from the perspective of TGA. *Energy*. **36**(2): 819-824.
- 285 Mhilu, C.F. (2014). Analysis of energy characteristics of rice and coffee husks blends. *International*  
 286 *Scholarly Research Notices in Chemical Engineering*. **2014**(1): 1-6.
- 287 Mishra, R.K. and Mohanty, K. (2018). Pyrolysis kinetics and thermal behavior of waste sawdust biomass  
 288 using thermogravimetric analysis. *Bioresource technology*. **251**(1): 63-74.
- 289 Mohammed, Y., Mustafa, M. and Bashir, N. (2013). Status of renewable energy consumption and  
 290 developmental challenges in Sub-Sahara Africa. *Renewable and Sustainable Energy Reviews*.  
 291 **27**(1): 453-463.
- 292 Noor, Z.Z., Yusuf, R.O., Abba, A.H., Hassan, M.A.A. and Din, M.F.M. (2013). An overview for energy  
 293 recovery from municipal solid wastes in Malaysia scenario. *Renewable and Sustainable Energy*  
 294 *Reviews*. **20**(1): 378-384.
- 295 Omari, A.M., Kichonge, B.N., John, R., Njau, K.N. and Mtui, P.L. (2014). POTENTIAL OF MUNICIPAL SOLID  
 296 WASTE, AS RENEWABLE ENERGY SOURCE-A CASE STUDY OF ARUSHA, TANZANIA. *sustainable*  
 297 *development*. **3**(4).
- 298 Pandey, B.K., Vyas, S., Pandey, M. and Gaur, A. (2016a). Characterisation of municipal solid waste  
 299 generated from Bhopal, India. *Curr. Sci. Perspect*. **2**(1): 52-56.
- 300 Pandey, B.K., Vyas, S., Pandey, M. and Gaur, A. (2016b). Municipal solid waste to energy conversion  
 301 methodology as physical, thermal, and biological methods. *Curr. Sci. Perspect*. **2**(1): 39-46.



- 302 Quina, M.J., Bontempi, E., Bogush, A., Schlumberger, S., Weibel, G., Braga, R., Funari, V., Hyks, J.,  
303 Rasmussen, E. and Lederer, J. (2018). Technologies for the management of MSW incineration  
304 ashes from gas cleaning: new perspectives on recovery of secondary raw materials and circular  
305 economy. *Science of the Total Environment*. **635**(1): 526-542.
- 306 Ryu, C. (2010). Potential of municipal solid waste for renewable energy production and reduction of  
307 greenhouse gas emissions in South Korea. *Journal of the Air & Waste Management Association*.  
308 **60**(2): 176-183.
- 309 Shahsavari, A. and Akbari, M. (2018). Potential of solar energy in developing countries for reducing  
310 energy-related emissions. *Renewable and Sustainable Energy Reviews*. **90**(1): 275-291.
- 311 Sharholly, M., Ahmad, K., Mahmood, G. and Trivedi, R. (2008). Municipal solid waste management in  
312 Indian cities—A review. *Waste management*. **28**(2): 459-467.
- 313 Smith, P., Martino, D., Cai, Z., Gwary, D., Janzen, H., Kumar, P., McCarl, B., Ogle, S., O'Mara, F. and Rice,  
314 C. (2007). Greenhouse gas mitigation in agriculture. *Philosophical transactions of the royal  
315 Society B: Biological Sciences*. **363**(1492): 789-813.
- 316 Sonobe, T. and Worasuwannarak, N. (2008). Kinetic analyses of biomass pyrolysis using the distributed  
317 activation energy model. *Fuel*. **87**(3): 414-421.
- 318 Tan, Y.L., Ahmed, M.J., Hummadi, E.H. and Hameed, B.H. (2019). Kinetics of Pyrolysis of Durian (*Durio  
319 zibethinus* L.) Shell Using Thermogravimetric Analysis. *Journal of Physical Science*. **30**(1).
- 320 Tsamba, A.J., Yang, W. and Blasiak, W. (2006). Pyrolysis characteristics and global kinetics of coconut  
321 and cashew nut shells. *Fuel Processing Technology*. **87**(6): 523-530.
- 322 Udomsri, S., Petrov, M.P., Martin, A.R. and Fransson, T.H. (2011). Clean energy conversion from  
323 municipal solid waste and climate change mitigation in Thailand: waste management and  
324 thermodynamic evaluation. *Energy for Sustainable Development*. **15**(4): 355-364.
- 325 Wilson, L., Yang, W., Blasiak, W., John, G.R. and Mhilu, C.F. (2011). Thermal characterization of tropical  
326 biomass feedstocks. *Energy Conversion and Management*. **52**(1): 191-198.
- 327 Wolfram, C., Shelef, O. and Gertler, P. (2012). How will energy demand develop in the developing  
328 world? *Journal of Economic Perspectives*. **26**(1): 119-38.

329