

3  
4 **Influence of mixing time on fresh and hardened**  
5 **cast-in-place concrete in southeastern Mexico**

6  
7  
8  
9  
10 **ABSTRACT**

11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37

An adequate mixing time in concrete casting allows to achieve a homogeneous mass and improve compressive strength and durability. However, the lack of standards for cast-in-place concrete causes that the builders use different mixing times according to the locality usages and customs, which results in a high variability of the expected quality. In this paper, fresh and hardened cast-in-place concrete was evaluated. Seven samples were tested with different mixing time using portable rotary drum mixer. The used materials were ordinary Portland cement, water and high absorption aggregates, fine and coarse, coming from a limestone crushing process. The results of the research showed that the mixing time and environmental temperature had no apparent influence on the slump of the mixtures, and trapped air and compressive strength increased slightly with increasing mixing time. Finally, it was found that the recommended mixing time, with rotation speed of 28 RPM, is 2.5 minutes, which differs from the common practice in the study area.

*Keywords: Mixing time, cast-in-place concrete, rotation speed, compressive strength, slump.*

**1. INTRODUCTION**

Concrete is a composite material that contains cement, water, aggregates and often, additives or additions. When these materials have been mixed and hydrated, they generate a chemical reaction forming a homogenous mass, a quality that improve compressive strength and durability. In addition to the water/cement ratio, and the quality of the materials, an important factor that influences the behavior of hardened concrete is the mixing time. The optimum mixing time depends in turn on the type and conditions of the mixer, rotation speed, load size, nature of the materials, and the environmental temperature, therefore, the most efficient mixing time should be determined in the field considering these variables [1]. In Mexico, the recommended mixing time by the NMX C-159-ONNCCE-1999 standard [2] is five minutes after all the materials were loaded, however, in the works, it is almost always about mixing the concrete as quickly as possible, which is due to economic issues, so determining the necessary minimum time is very important. Some minimum mixing times have been specified in several standards and regulations according to the capacity of the mixer, but generally refer to ready-mix concrete. The recommended minimum mixing times for low capacity mixers, are indicated in Table 1.

38  
39

**TABLE 1** Minimum mixing times for low capacity mixers

Loading capacity (m <sup>3</sup> )	Minimum time (min)	Reference
0.76	1.0	[3, 4]
<1.5	1.5	[5]
--	1.5	[6]

40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53

According to Neville and Brooks [7], a mixing time of less than one minute causes problems of uniformity and low strength in the concrete. Conversely, a greater time than two minutes does not necessarily mean that there is an improvement in those properties. Other authors such as Charonnat and Beitzel [8] in countries of the European Union, as well as Trejo and Chen [9] in the United States, have focused on the study of time and efficiency of the mixing process in prolonged periods because the use of ready-mixed concrete has a high demand. However, in many countries with less technological development, cast-in-place concrete for medium and small works is a frequent practice, carried out in various ways due to the lack of precise specifications to achieve adequate characteristics of workability and compressive strength. This has led to the development of this research, whose main objective was to determine the most efficient mixing time and its relationship with the properties of fresh and hardened cast-in-place concrete, based on a field study, carried out to determine times and rotation speed of the portable mixers used in the works.

54  
55

## 2. MATERIALS AND METHODS

56  
57

### 2.1 Previous field study

58  
59  
60  
61  
62  
63  
64  
65  
66  
67  
68  
69  
70  
71  
72  
73

This stage was aimed to obtain reliable information about mixing times, rotation speeds and the characteristics of the used mixers. Also, direct interviews were applied to local builders and construction workers for detect those works where cast-in-place concrete was being used, which constituted the size of the population to be observed, using an intentional deterministic sampling. The study was carried out in Chetumal City, located in the southeastern of Mexico, whose population is 151,243 inhabitants [10]. It has sub-humid warm weather most of the year, being the average annual temperature of 26.4° C. The technical data of the portable rotary drum mixer and concrete casting practices were determined by direct observation. Mixing times were measured with a stopwatch from which last material was discharged into the mixer. The technical data were processed in those cases where some external factors modified the continuity of the work, such as workers distractions, lack of material and other delays, in this way the averages of rotation speed and mixing time were obtained for the control specimens. The location of the monitored works in the city territorial extension can be seen in Figure 1.

74  
75  
76  
77



**Figure 1. Monitored works location**

78 **2.2 Materials**

79

80 The used materials were ordinary portland cement, water, and fine and coarse aggregates,  
 81 both obtained by crushing limestone from a local quarry, whose properties were determined  
 82 according to ASTM standards [11], summarized in Table 2.

83

84

85


**TABLE 2** Aggregates properties

Property	Coarse aggregate	Fine aggregate
Loose unit weight (kg/m <sup>3</sup> )	1265	1462
Compact unit weight (kg/m <sup>3</sup> )	1343	--
Specific gravity	2.5	2.7
Absorption (%)	4.3	1.4
Abrasion (%)	35	--
Maximum size (mm)	19	--
Fineness modulus	--	2.9

86

87 As expected, the characteristics of the aggregates showed typical unfavorable conditions of  
 88 the materials of limestone origin [12]. On the other hand, the granulometric study of the  
 89 coarse aggregate indicated a reduced amount of particles that pass the 9.5 mm sieve  
 90 (Figure 2). The selected fine aggregate for this investigation had an acceptable  
 91 granulometry, except for the amount of material that passes the No. 50 sieve equivalent to  
 92 50 μm (Figure 3).

93

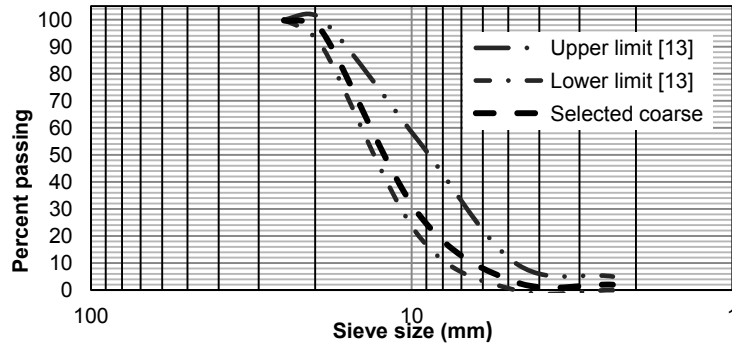


94

95

96 **Figure 2. Granulometry of coarse aggregate**

97

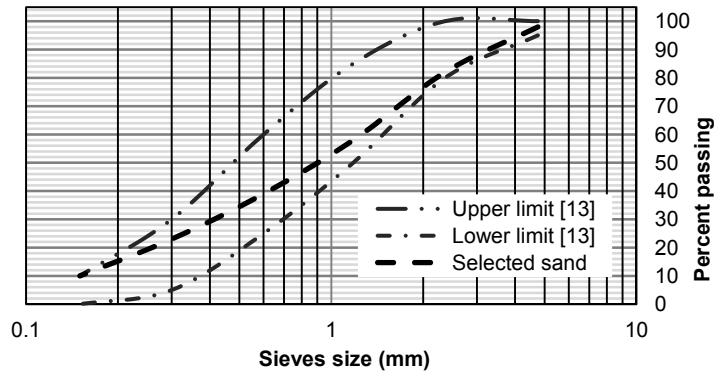

98

99

**Figure 3. Granulometry of fine aggregate**

## 100 2.3 Experimental Details

101 The selected rotation speeds according the previous field study, were 25, 70, 90, 100, 110,  
102 120 and 140 RPM, each with its equivalent mixing time. These values were considered as  
103 independent variables; to identify them they were assigned the letter S (sample) followed by  
104 a consecutive number, where S1 corresponded to the control sample. The dependent  
105 variable was compressive strength (Fc). Mixture design was performed based on ACI  
106 method [14], where the water/cement ratio (w/c) was 0.45 with 75 mm of slump. The relative  
107 amounts of the materials, before daily moisture corrections, are indicated in Table 3. The  
108 fresh concrete tests were slump and trapped air. For Fc tests, cylindrical specimens of 15 x  
109 30 cm were cast, which were subjected previously to a process of moist curing by immersion  
110 for 28 days at 3, 7, 14, 28 and 90 age days.

111  
112

**Table 3. Mixtures design**

Material	Relative amounts (kg/m <sup>3</sup> )
Water	205
Cement	456
Coarse aggregate	822
Fine aggregate	862

113  
114  
115

## 114 3. RESULTS AND DISCUSSION

116 In the preliminary field study, fourteen works were observed, where the average time for  
117 casting was 0.9 minutes with a rotation speed of 25 RPM in each batch. A rotary drum  
118 portable mixer with 50 kg load capacity and 28 RPM speed was used. This information was  
119 useful to set the concrete mixing time and choose the laboratory equipment. The obtained  
120 results for the fresh concrete, including the environmental temperature during the casting, as  
121 well as the rotation speeds and equivalent mixing times are indicated in Table 4.

122  
123

**Table 4. Fresh concrete properties**

Sample	RPM	Mixing time (min)	Slump (mm)	Trapped air (%)	Environmental Temperature (°C)
S1	25	0.9	50	3.4	27
S2	70	2.5	50	3.1	29
S3	90	3.2	55	3.6	29
S4	100	3.6	40	3.7	27
S5	110	3.9	30	3.2	28
S6	120	4.3	46	3.4	31
S7	140	5.0	40	3.4	31

124

125 As can be seen in Table 4, trapped air varied slightly, with no apparent influence of mixing  
126 time. Regarding the slump, it is observed that all the samples were below the design value,  
127 being more evident in those with longer mixing time. Similar values were found by Gonzalez  
128 et al. [15] when w/c ratios were less than 0.47. The ambient temperature varied in a range of  
129 4 °C without showing any influence on the properties.

130 The Fc results at different ages, revealed a rapid growth tendency, because on the seventh  
131 day, they reached more than 80% of their optimum resistance, which denotes good  
132 efficiency of the mixing process. The sample with the longest mixing time (S7) was the one  
133 that reached the highest Fc at the age of 28 days, 20% more than the control sample (S1),  
134 which can be seen in Figure 4.

135

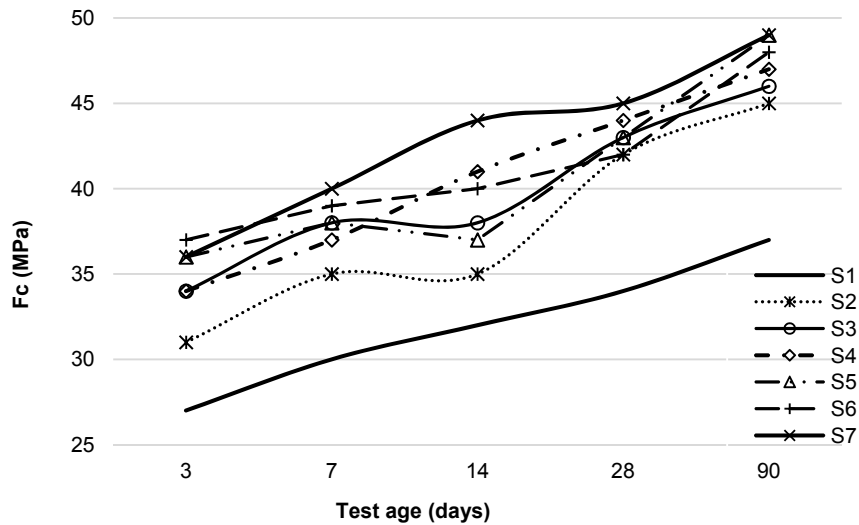


Figure 4. Compressive strength at different ages

These results can be contrasted with the ready-mix concrete data, informed by Kirca et al. [16] and Trejo and Chen [17], who also reported increases in the  $F_c$  when the mixing time was increasing. According Equation 1, the real influence of the mixing time on the  $F_c$  was determined with an Efficiency Index (EI), which was calculated from the ratio between  $F_c$  differentials ( $\Delta F_c$ ) and mixing time differentials ( $\Delta t$ ) of each sample under study compared to the control sample.

$$EI = \Delta F_c / \Delta t \quad (1)$$

The complete outcomes at the age of 28 days can be seen in Table 5, where the most recommended mixing time is 2.5 minutes (S2) according EI.

Table 5. Efficiency index of the samples

Sample	$F_c$ (MPa)	Time (min)	$\Delta F_c$	$\Delta t$	EI
S1	34	0.9	--	--	--
S2	42	2.5	8	1.6	5.0
S3	43	3.2	9	2.3	3.9
S4	44	3.6	10	2.7	3.7
S5	43	3.9	9	3.0	3.0
S6	42	4.3	8	3.4	2.4
S7	45	5.0	11	4.1	2.7

Lastly, a statistical analysis for  $F_c$  data was carried out. The normality was verified with shape coefficients: -1.85 for asymmetry and -0.18 for kurtosis, which were within the expected range of a normal distribution ( $\pm 2$ ). Subsequently, the results for ANOVA showed that  $P < .001$ . Since the significance was less than .05, indicating the difference between the means of the seven variables or samples under study, a multiple-rank test was performed using the LSD method to identify homogeneous groups among the means [18]. As result, a marked difference was observed between the control samples (S1) and the rest, a strong

161 similarity between the samples S3, S4, and S5, and some similarity of the samples S6 and  
162 S7 with the three previous ones.

163

#### 164 **4. CONCLUSIONS**

165

166 The present work constitutes one of the first efforts in establishing appropriate mixing times  
167 for cast-in place concrete, using high absorption limestone aggregates. According to the  
168 results of the research, the following conclusions can be drawn:

169 The mixing time and environmental temperature had no apparent influence on the slump of  
170 the mixtures. Trapped air and compressive strength increased slightly with increasing mixing  
171 time. The suggested mixing time corresponded to 2.5 minutes with a speed of 28 RPM,  
172 which differs from the common practice established in the previous field study.

#### 173 **REFERENCES**

174

- 175 1. Mindess S, Young JF, Darwin D. Concrete. 2nd ed. Upper Saddle River (NJ): Prentice  
176 Hall. 2003.
- 177 2. NMX C-159-ONNCCE-1999. Industria de la Construcción-Concreto-Elaboración y  
178 Curado de Especímenes en el laboratorio. México: Organismo Nacional de  
179 Normalización y Certificación de la Construcción y Edificación, S. C. 1999. Spanish.
- 180 3. ASTM C 94-13. Standard Specification for Ready Mixed Concrete. West  
181 Conshohocken, (PA): American Society for Testing and Materials. 2013.
- 182 4. ACI 304 R-00. Guide for Measuring, Mixing, Transporting, and Placing Concrete.  
183 Farmington Hills (MI): American Concrete Institute. 2000.
- 184 5. NMX C-403-ONNCCE-1999. Industria de la Construcción-Concreto Hidráulico para Uso  
185 Estructural. México: Organismo Nacional de Normalización y Certificación de la  
186 Construcción y Edificación, S. C. 1999. Spanish.
- 187 6. ACI Committee 318. Building Code Requirements for Structural Concrete and  
188 Commentary. Farmington Hills (MI): American Concrete Institute. 2014.
- 189 7. Neville AM, Brooks JJ. Tecnología del concreto. 1st ed. México: Trillas. 2010. Spanish.
- 190 8. Charonnat Y, Beitzel H. Efficiency of concrete mixers towards qualifications of mixers.  
191 1997; Mater Struct, RILEM, Supplement March. 32-28.  
192 <https://doi.org/10.1007/BF02539273>.
- 193 9. Trejo D, Chen J. Effects of Extended Discharge Time and Revolution Counts for Ready-  
194 mixed Concrete. Research Project SPR. Final Report. Oregon State University. 2014.
- 195 10. Instituto Nacional de Estadística y Geografía. Censo de Población y Vivienda 2010.  
196 2013. <http://www.inegi.org.mx/est/contenidos/proyectos/ccpv/cpv2010/default.aspx>.  
197 Spanish.
- 198 11. ASTM Book of Standards, Construction: Concrete and Aggregates, American Society  
199 for Testing and Materials, West Conshohocken, PA, USA, 2010.
- 200 12. Trejo-Arroyo DL, Acosta KE, Cruz JC, Valenzuela-Muñiz AM, Vega-Azamar RE,  
201 Jiménez LF. Influence of ZrO<sub>2</sub> Nanoparticles on the Microstructural Development of  
202 Cement Mortars with Limestone Aggregates. Appl. Sci. 2019; 598(9): 12.  
203 <https://doi.org/10.3390/app9030598>
- 204 13. ASTM C 33-08; Standard Specification for Concrete Aggregates, American Society for  
205 Testing and Materials, West Conshohocken, PA, USA, 2008.
- 206 14. ACI 211.1; Standard Practice for Selecting Proportions for Normal, Heavyweight and  
207 Mass Concrete, American Concrete Institute, Farmington Hills, MI, USA, 1998.

- 208 15. González-Díaz E, Jaizme-Vega E, Jubera-Pérez J. Assessment of the influence of the  
209 effective water-cement ratio on the workability and strength of a commercial concrete  
210 used for the construction of concrete caissons. Rev. Constr. 2018; 32(2): 239-231.  
211 <https://doi.org/10.7764/RDLC.17.2.231>.
- 212 16. Kirka Ö, Turanlı L, Erdoğan T. Effects of Retempering on Consistency and Compressive  
213 Strength of Concrete Subjected to Prolonged Mixing. Cem. Concr. Res. 2002; 32(3):  
214 445-441. [https://doi.org/10.1016/S0008-8846\(01\)00699-8](https://doi.org/10.1016/S0008-8846(01)00699-8).
- 215 17. Trejo D, Chen J. Influence of Mixing Time on Fresh and Hardened Concrete  
216 Characteristics. ACI Mater. J. 2015; 112 (6): 754-745.  
217 <https://doi.org/10.14359/51687396>.
- 218 18. Montgomery DC. Diseño y Análisis de Experimentos, Limusa Wiley: México, 2011.  
219 Spanish.  
220



© 2019 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).

221