

Optimization of process parameters for the treatment of Crude oil spill polluting water surface by sorption technique using fatty acid grafted ogbono shell as a sorbent

Onwu D.O¹, Ogbodo O, Nick², Ogbodo N, Cordelia³, Christian O, Asadu⁴ and Onoh I, Maxwell⁵

^{1,2,3,4,5}Department of Chemical Engineering, Enugu State University of Science and Technology, P.M.B 01660 Enugu Nigeria

Corresponding author: aasadu@yahoo.com

ABSTRACT

This work focuses on the optimization of the adsorption technique using fatty acid grafted ogbono shell for the removal oil from polluted water surface. The shell was carbonized at a temperature of 600°C for 4h and then further modified with stearic acid. The surface morphology of raw and grafted ogbono shell was studied by Scanning Electron microscope (SEM) while functional groups were investigated by Fourier Transform Infra-red Spectroscopy (FTIR). Proximate analysis was carried out to determine the surface area of the agro wastes before and after modification. The process parameters were optimized using response surface methodology. Physiochemical characterization of the adsorbents showed that surface area increased significantly after carbonization and modification. SEM and FTIR results revealed that more micro porous surfaces were created on the surface of the adsorbent after modification. The theoretical optimum conditions for oil spill treatment include 10 min time, 60 °C temperature, 1.4 g dosage and pH 3 with removal percentage of 78.77% and the actual percentage in good agreement of 76.40%.

Keywords: Optimization, ogbono shell, crude oil adsorption, surface modification

INTRODUCTION

Crude oil is a combustible liquid found in the earth's sedimentary mantle and is basically composed of a complex mixture of hydrocarbons with its color ranging from brown to almost black depending on the structure of the resinous substances it contains (Uzoije et al., 2011). Over the years, crude oil spill and its concomitant pollution have been on the front burner in

environmental issues over the world and in particular the rich Niger Delta of Nigeria (Uzoije et al., 2011). Crude oil spillage results when oil has been released into the environment (Ali et al., 2012). In seawater and soil are usually as a result of exploration or transportation or storage activities (Annunciado et al., 2005; Baars, 2002). The Spillage can be broadly categorized into four groups, namely minor, medium, major and disaster (Banerjee, 2006). The most frequent of these is the minor spillage which is oil discharge less than 25 barrels in land waters or less than 250 barrels on land, offshore and coastal water (Behnood et al., 2013). This category of spill contributes more to the total volume of annual spillage than other categories (Chung et al., 2011).

Clean-up is necessary after a spill for the protection of the environment and human health and can be managed by a wide range of tools and techniques among which include; chemical remediation, bioremediation, phytoremediation, thermal desorption, adsorption and land fill in the case of soil spillage. Adsorption technique is of greater interest due to its cheapness and convenience (Sayed et al., 2003). Natural sorbents and varieties of organic vegetable waste products; such as peat moss, wood, cotton, rice straw, corncobs and kapok have been recently gained an appraisal both internationally and locally as an effective sorbents in oil spill treatment (Nwadiogbu et al., 2016; Choi and Cloud, 1992; Deschamop et al., 2003). These agro wastes are at no cost and available locally. This work focuses on optimizations of the process parameters using response surface methodology (RSM). (RSM) which is a statistical tool designed specifically for this purpose. Its usage depicts the effect of independent factors on the results or expected results. The input elements or factors are the independent variables while the response(s) or the outputs are the dependent variables (Datta, 2011). RSM relates item properties by utilizing regression equation that portrays interrelations between information factors and item properties (Adeyanju et al., 2016). The most often used RSM are central composite design (CCD) and Box Behnken design (BBD) because they are more user friendly and also relates products properties by using regression equations that describe interrelations between input variables and product properties. Therefore, the aim of this study is to optimize the use of esterified ogbono shell (agro wastes) as an adsorbent in the remediation of crude oil layer polluted water surface using BBD design.

Materials and method

Materials

The major raw material (Ogbono shells) was collected from Akpoga Nike in Enugu State Nigeria. The shells were first washed and dried under the sun for one week. After which, the shells were grounded using a commercial grinder at Oye Market in Emene, Enugu State Nigeria.

Other materials used included; Crude oil collected from Shell oil location Rivers State Nigeria, distilled water, Sieving net, analytical grade sodium hydroxide (NaOH), H₂SO₄, HCl, stearic acid, n-hexane purchased from Conraws Chemical Ltd, Presidential Road, Enugu Nigeria. .

Methods

Preparation of Carbonized Adsorbent (Ogbono Shells)

The dried biomass (Ogbono shells) was carbonized in a muffle furnace at 600°C for 4 hours respectively. After the carbonization, the samples were cooled and stored in dry transparent containers (glass bottles) for further use (Angelova et al., 2011).

Activation of the carbonized ogbono shell by Esterification

Carbonized samples of the biomass (ogbono shell) were treated differently with 0.5g of stearic acid in 200 mL of n-hexane containing two drops of concentrated H₂SO₄ as a catalyst. The mixture was refluxed in Dean- Stark apparatus at 65± 2°C and for 4h. After reaction, the esterified acid-grafted ogbono shells were washed several times with n- hexane. The fatty acid grafted biomass was oven dried at 110°C for 12 h (Banerjee et al., 2006) and kept in dry tightly closed bottles for further use. The weight percentage can be calculated as follows.

$$\text{Weight percentage gain} = \frac{\text{Weight gain}}{\text{Original weight}} \times 100 \quad (1)$$

Characterization of the raw and modified biomass

The surface morphology of the (raw and modified) biomass was studied using Model 302 Hitachi High Field Emission Scanning Electron Microscope and the images at 1mm and 150 magnifications. The method employed by Nwabanne and Igbokwe (2008) was adopted to carry out Fourier Transformed Infrared analysis of raw and modified biomass (Ogbono shell) using BUCK model 500 M infrared spectrophotometer. The sample was prepared using KBr and the analysis was done by scanning the sample through a wave number range of 500 to 4000 cm⁻¹. The proximate analysis parameters and the method of analysis were according to the American Society for Testing and Materials (ASTMD 5142, 3174, 872 and 3175 for moisture, ash, volatile and fixed carbon respectively) (Diadem, 2012)

Adsorption Experiment

The sorption of crude oil contaminated water was carried out following the method described by Banerjee et al. (2006). Exactly 50ml of water was measured inside a 100ml beaker. A certain amount of crude oil (0.1-1.4g) depending on the oil/water ratio for a particular run was added into the beaker. The oil/water mixture was manually stirred for different period of time (between 10 to 50 minutes) to ensure proper dispersion of the oil in water. 0.2g of the modified adsorbent was weighed into the beaker. The beaker containing the sorbent, oil and water was put into a water bath at different temperature in the range of (30 to 90°C). The mixture was stirred again for different experimented time (between 10 to 50 minutes), depending on the particular run. After that the mixture was filtered through a net of approximately 250µm. The weight of the net before and after the filtration was recorded. Meanwhile, the net after the filtration was allowed to stay for 24h before the final weight was taken to allow all the moisture to evaporate.

Percentage removal was also calculated according to the equation below:

$$\% \text{ removal} = \frac{(C_o - C_e)}{C_o} \times 100 \quad (2)$$

$$q_e = \frac{(C_o - C_e)}{M} V \quad (3)$$

C_o = Initial oil concentration (mg/l)

C_e = Equilibrium Concentration oil at certain time

Q_e = Equilibrium adsorption in (mg/g)

V = Volume of the aqueous mixture in cm^3

M = Mass of the activated biomass (Esterified ogbono shell) in (g)

Design of Experiment using BBD

The sorption of the crude oil layers by activated ogbono shell was optimized using Box Benken design (BBD) and RMS methods. The independent variables studied were Time X_1 (min), temperature X_2 (°C), adsorbent dosage X_3 (g), and pH X_4 . The time range of 10 to 60 min, the temperature range of 30 to 70 °C, dosage range of 0.2 to 1.4 and pH range of 3 to 11 were selected. The coded and uncoded levels of these independent variables are shown in Table 1. The experimental design was based on BBD. This was done to determine the best conditions for

optimum sorption of the oil onto activated biomass. Equally, this helps to examine the interactive effects of the four important factors (Time, Temperature, dosage and pH). These factors were the independent variables while the percentage of oil adsorbed or removed (%R) were the dependent variables or responses. Using the BBD (a statistical package in Minitab software version 17.1.0) involves varying the independent variables at three different levels (-1, 0, +1). In this work, a set of 27 experiments were performed. Table 2 shows the run order, variable conditions and the columns for the experimental, predicted and residual values of the oil layer sorption unto activated biomass.

Table 1: Independent variables with three different levels

Variables	Symbol	Level		
		Low	Centre	High
Time (mins)	X ₁	10	35	60
Temperature (°C)	X ₂	30	60	90
Dosage (w:w)	X ₃	0.2	0.8	1.4
pH	X ₄	3	7	11

Table 2: Design matrix with responses for the sorption of oil from surface water onto Esterified Ogbono shell

Std	Run	Time: X ₁ mins	Temp:X ₂ °C	Dosage:X ₃ g	pH:X ₄	Coded values X ₁ X ₂ X ₃ X ₄	%Sorption Experiment al	%Sorption Predicted
5	1	35	60	0.2	3	1 0 0 -1 -1	21.34	23.56
13	2	35	30	0.2	7	1 0 -1 -1 0	36.10	32.56
20	3	60	60	1.4	7	1 1 0 1 0	27.30	23.11
9	4	10	60	0.8	3	1 -1 0 0 -1	28.90	30.12
1	5	10	30	0.8	7	1 -1 -1 0 0	55.75	56.22
10	6	60	60	0.8	3	1 1 0 0 -1	17.30	17.00
3	7	10	90	0.8	7	1 -1 1 0 0	26.34	23.66
14	8	35	90	0.2	7	1 0 1 -1 0	26.11	26.77
7	9	35	60	0.2	11	1 0 0 -1 1	21.88	21.34
24	10	35	90	0.8	11	1 0 1 0 1	29.55	28.97
12	11	60	60	0.8	11	1 1 0 0 1	14.20	14.79
26	12	35	60	0.8	7	1 0 0 0 0	28.07	29.66
16	13	35	90	1.4	7	1 0 1 1 0	26.11	26.78
21	14	35	30	0.8	3	1 0 -1 0 -1	37.23	36.97
19	15	10	60	1.4	7	1 -1 0 1 0	76.40	78.77
2	16	60	30	0.8	7	1 1 -1 0 0	15.80	16.34
25	17	35	60	0.8	7	1 0 0 0 0	24.80	29.66
11	18	10	60	0.8	11	1 -1 0 0 1	30.45	27.89
22	19	35	90	0.8	3	1 0 1 0 -1	12.33	10.14

18	20	60	60	0.2	7	1	1	0	-1	0	22.55	23.11
8	21	35	60	1.4	11	1	0	0	1	1	19.60	21.34
4	22	60	90	0.8	7	1	1	1	0	0	29.40	29.89
23	23	35	30	0.8	11	1	0	-1	0	1	12.34	13.70
6	24	35	60	1.4	3	1	0	0	1	-1	24.23	23.56
15	25	35	30	1.4	7	1	0	-1	1	0	61.67	62.56
17	26	10	60	0.2	7	1	-1	0	-1	0	32.33	36.22
27	27	35	60	0.8	7	1	0	0	0	0	31.23	29.66

Results and Discussion

Proximate analysis of the raw and modified biomass

The characteristics of raw and modified biomass were shown in Table 3. From the Table, it can be seen that the raw biomass (ogbono shell) have low fixed carbon, surface area and high volatile content and as such suggest that the sample requires activation. Increase in fixed carbon and reduction in volatile matter of the **activated biomass together with the modification with stearic acid to increase the number of micropores improved the surface area of biomass for adsorption from 114 cm² to 190.5 cm² similar to the results of acetylated ogbono shell by Alothman et al., 2011. The pH of the carbonized and modified ogbono shell was found to be slightly alkaline when compared with the pH of raw ogbono shell which is acidic.**

Table 3: Physical properties of the raw and modified ogbono shell

Adsorbents	Ash content (%)	Volatile matter (%)	Carbon content (%)	Surface area(m ² /g)	pH
Raw ogbono shell	7.4	28.6	56.5	114	6.9
Carbonized ogbono shell	5.7	21.4	64.2	129.4	7.1
Esterified ogbono shell	5.6	19.3	69.4	190.5	7.2

SEM Analysis Results

SEM Analysis is used to study the morphological compositions of the biomass before modification and after modification. As shown in fig 1, there were more pore spaces in the carbonized and activated adsorbents than in the unmodified biomass. Availability of pore spaces favors adsorption process. The surface morphologies of the raw biomass (Ogbono shells), and

esterified biomass were presented as shown in fig 1 and 2. It was observed from fig. 1 that the samples were internally bonded together. It can also be observed from the figures that a bulk of microstructure which in turn is composed of a homogeneously distributed network comprised of small filamentous and fistulous crystallites showing the presence of minerals. In the matrix, Luminous and non-luminous features can be seen. These features indicate the presence of minerals distributed in the organic matrix and as surface coverage. From fig 2, the surface is loosed and some features such as fissures, cleats, cracks and veins can be seen showing that the action of heat and acid did lots of harm to the surface and the surface is no longer as intact as shown in fig 1. **Some minute fissures and cracks, however an evident of the changes that has taken place.** These changes in microstructures may not be unconnected to the removal of some minerals from the activated biomass thereby increasing the **microporous** surface. The surface is bright and mostly protracted. **A number of micropores** has been increased and provides strong evidence that significant amounts of organic elements are being removed thereby increasing the number of micro pores



Fig 1: SEM image of un-carbonized ogbono shell @ 100µm

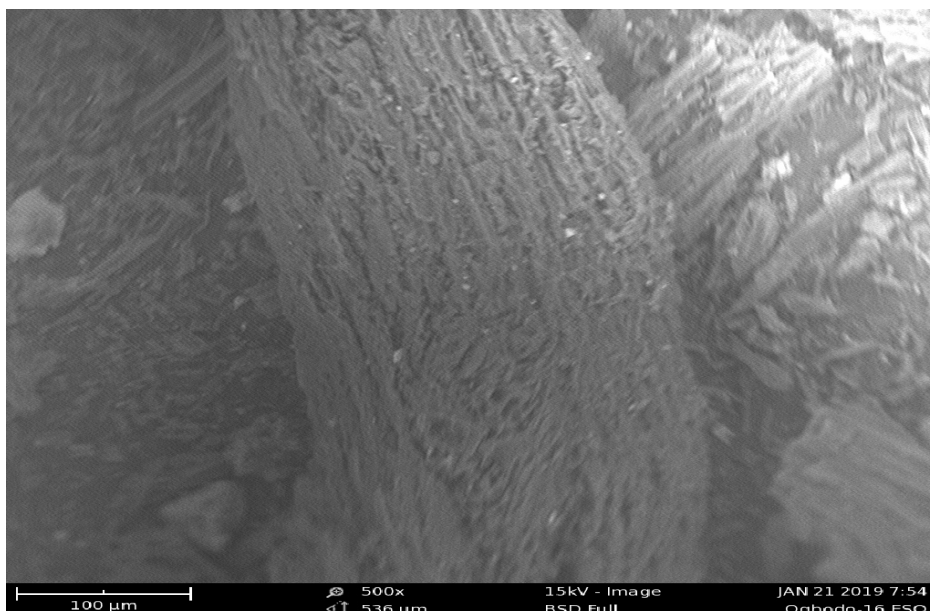


Fig 2: SEM image of esterified ogbono shell@ 100 μ m

Fourier Transform infrared (FTIR) of the modified and unmodified biomass

Fourier transform infrared spectra of the raw biomass, carbonized biomass, and esterified biomass are presented in Fig. 3-5. The bands were assigned according to those in previous literature (Starsinic et al., 1984; Supaluknari et al., 1998). It was observed that numerous functional groups and the major functional groups present are O-H, N-H, N-CH₃, C=C-C, C-Cl, Si-O-Si. Petroxides bands stretches between 9650-1095cm⁻¹, Aromatic phosphate P-O-C stretches between 1300-1390cm⁻¹, Aromatic C-H in plane bend, Silicon ozy compounds Si-O-Si stretches between 1125-1295cm⁻¹, C-Cl stretch, alkyne C-C bend lies between 700-900cm⁻¹, hydroxyl group OH stretch was observed between 4000-3650cm⁻¹, primary amine group NH stretches between 3200-3450cm⁻¹, Aliphatic secondary amine NH stretches between 3150-3200cm⁻¹, Normal polymetric stretch of hydroxyl group lies between 3050-3100cm⁻¹, Methylamino acids N-CH, C-H stretches between 2550-2950cm⁻¹, Cyanide ion, thiocyanide ion stretches between 1990-2000cm⁻¹, Isocyanate N=C=O stretches between 2290-2550cm⁻¹, Isothiocyanate -CNS bond stretches between 1600-1795cm⁻¹, **Conjugated ketones**, open chain acids anhydrides stretches between 1600-1750cm⁻¹, the bending of the hydroxyl group was further observed at the stretch between 1450-1595cm⁻¹. Fig 3 showed that the entire spectrum had more or less similar broad characteristic absorption bands. All the absorption bands were unresolved indicating that the material constituents had either large particle size or a contained

polymeric unit which shows that the volatile matter is still intact. Esterification of the carbonized biomass has better modification with removal of volatile matter thereby creating more pores for oil adsorption as shown in fig. 5 indicating that the picks are more resolved than those as shown in Fig. 3, this further proved that esterification is effective in removing volatile matter and increasing micro pores on the surface of the adsorbents. The change in absorption and frequency in the spectrum peaks shows how the several treatment conditions affect the structure of the biomass .The functional groups indicate that the biomasses are organic compound which are hydrophobic and olephilic. This could be the reasons why they were able to remove the oil from water surface. Upon comparing the spectrum; it was observed that all the samples showed a remarkable absorption near 1440cm^{-1} . This indicated the strong presence of ethylene and methyl groups in the samples. The bands at 1541cm^{-1} and 1442cm^{-1} is normally present in organic substance (biomass) with more lignin content. The band was shifted from strong absorption to medium intensity in the spectra of stable product. This reveals the effectiveness of modification of biomass using esterification.

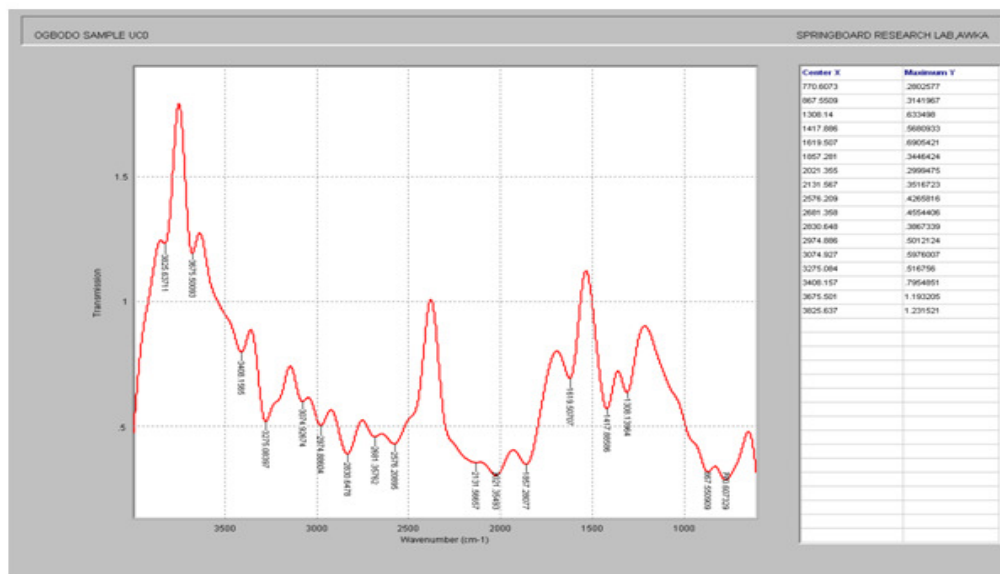


Fig 3: FTIR spectra for uncarbonized ogbono shell

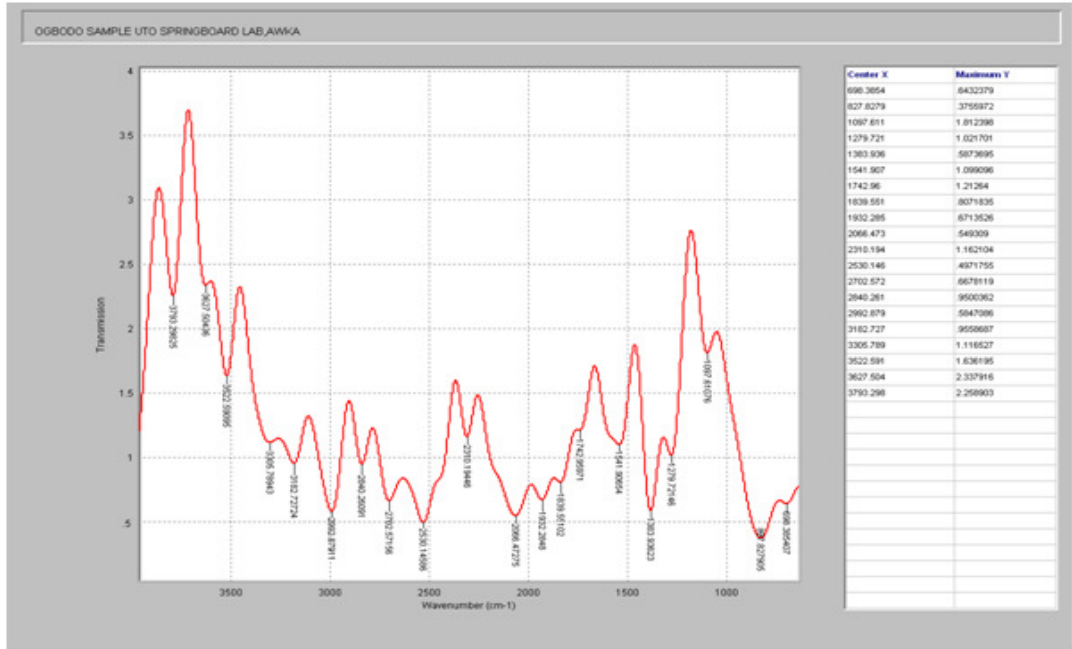


Fig 4: FTIR spectra for carbonized ogbono shell

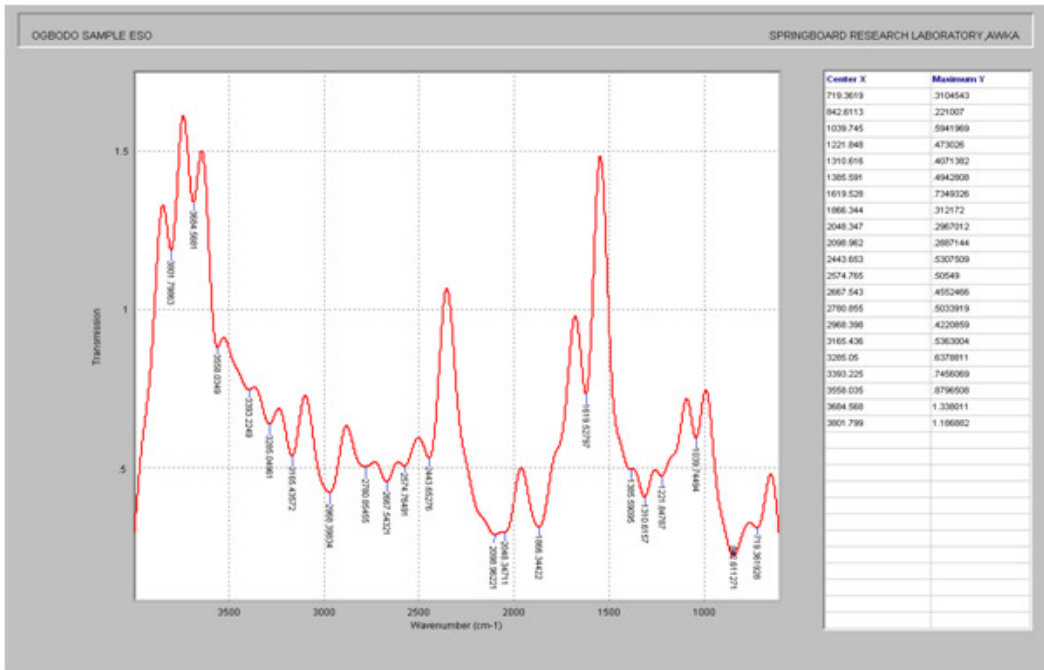


Fig 5: FTIR spectra for esterified ogbono shell

Statistical analysis of the sorption process using RSM

BBD was used with the process to determine optimum conditions for crude oil sorption. A set of 27 experiments was performed with the adsorbent (esterified ogbono shell) using a statistical

package Minitab software version 17.0. During analysis, it was discovered that the major response in which the main parameters or factors were significant at 0.05 was percentage removed (%R). The optimization analysis was therefore based on percentage removal as the major response. The experiments were performed in random to avoid systematic error. The design matrix and output responses for the sorption of crude oil were presented in Table 2. The responses obtained from various runs are significantly exceptional which implies that each of the factors have substantial effect on the response.

Analysis of variance (ANOVA) for the sorption of oil layer onto fatty acid grafted ogbono shell

The response values in Table 2 were analyzed using statistical package Minitab software (Minitab version 17.0). The F-value tests were performed using the ANOVA to calculate the significance of each type of model. Based on the results of F-value, the highest order model with significant terms which shows the most accurate relationship between parameters was be chosen. Besides evaluating the significance, the adequacy of the models was evaluated by applying the lack-of-fit test. This test was used in the numerator in an F-test of the null hypothesis and indicates that a proposed model fits well or not. The test for lack-of-fit compares the variation around the model with pure variation within replicated observations. This test measured the adequacy of the different models based on response surface analysis (Chauhan and Gupta, 2004)). The sum of square, the degree of freedom, the mean square, the F-values were shown in Table 4.

Table 4: Analysis of Variance (ANOVA) for the sorption of oil onto esterified ogbono shell

Source	DF	Seq SS	Contribution	Adj SS	Adj MS	F-Value	P-Value
Model	6	1794.50	93.98%	1794.50	299.084	52.08	0.000
Linear	3	630.20	33.01%	630.20	210.065	36.58	0.000
X ₁	1	515.09	26.98%	515.09	515.092	89.70	0.000
X ₂	1	100.34	5.26%	100.34	100.341	17.47	0.000
X ₄	1	14.76	0.77%	14.76	14.763	2.57	0.025
X ₄ ²	1	347.35	18.19%	347.35	347.346	60.49	0.000
X ₁ X ₂	1	373.65	19.57%	373.65	373.649	65.07	0.000
X ₂ X ₄	1	443.31	23.22%	443.31	443.313	77.20	0.000
Error	20	114.85	6.02%	114.85	5.742		
Lack-of-Fit	18	94.17	4.93%	94.17	5.232	0.51	0.832
Pure Error	2	20.67	1.08%	20.67	10.337		
Total	26	1909.35	100.00%				
R-sq	R-sq(adj)	PRESS	R-sq(pred)				
93.98%	92.18%	209.018	91.05%				

Multiple regression analysis was employed as a tool in this work to for the assessment of the effect of independent variables (Time, temperature, dosage and pH) on the dependent variables (%Sorption). % Sorption by the activated biomass (esterified ogbono shell) was analyzed using multiple regression method to fit second order polynomial equations. The second order polynomial equations developed after analysis of percentage sorption as a function of the actual values of Time (X₁), temperature (X₂), dosage (X₃) and pH (X₄) are as follows;

$$\begin{aligned}
 (\%Sorption)_{\text{Esterified ogbono shell}} = & 88.36 - 1.0353 X_1 - 1.1615 X_2 + 0.77 X_4 + 0.01289 X_1 X_2 \\
 & + 0.08773 X_2 X_4 - 0.4511 X_4^2
 \end{aligned}
 \tag{4}$$

Regression coefficients of the intercept, linear, quadratic and interaction terms of each model were presents in Table 4. The coefficient of determination (R²) obtained for the percentage sorption of oil by esterified ogbono shell was 93.98%. These result shows that more that 93% of the overall system variables can be explained by the quadratic models of equation 4. Higher values of F-ratio and lower p-values indicated higher significance of the model or model terms. The models significance was tested at p<0.05.

It was observed that the model p-value was 0.000. This indicates that the model is very significant and could be very efficient in predicting the system response (sorption of oil by activated biomass). The F-values was also observed to be 52.08 for acetylated ogbono shell. This value was found to be very high and as such, show that the model is highly significant above 93% confidence level. Table 4 shows that the linear terms of time (X_1), temperature (X_2) and pH (X_4) as well as interactive terms of time and temperature (X_1X_2), temperature and pH (X_2X_4) together with quadratic term of pH (X_4^2) were all significant with p-values ($p < 0.05$). However, the adjusted coefficient of regression ($Adj R^2$) and the predicted coefficient of regression ($Pred R^2$) were found to be, 92.18% and 91.05%. These results are indication of the model significance and also indicate that the quadratic model provided an excellent explanation for the relationship between the independent variables and the corresponding response.

The models adequacy was additionally checked from the normal residual plots as shown in Fig 6. It can be seen from the figure that the residual followed the normal distribution and the assumption of normality is somewhat valid. The data were also analyzed to check the correlation between the experimental and predicted sorption (%R). The experimental values were the measured response data for the runs designed by the Box Benkhen model on the platform of Minitab software version 17.0, while the predicted values were obtained by calculation from equation 4. Also, the points were closely distributed to the **straight line** of the plot ($R^2 = 93.98\%$). This confirms the good relationship between the experimental values and the predicted values as shown in Table 2. Some small scatter like an “S” shape is always expected which shows a normal distribution of experimental data points within the straight line. These plots equally confirmed that the selected model was adequate in predicting the response variables.

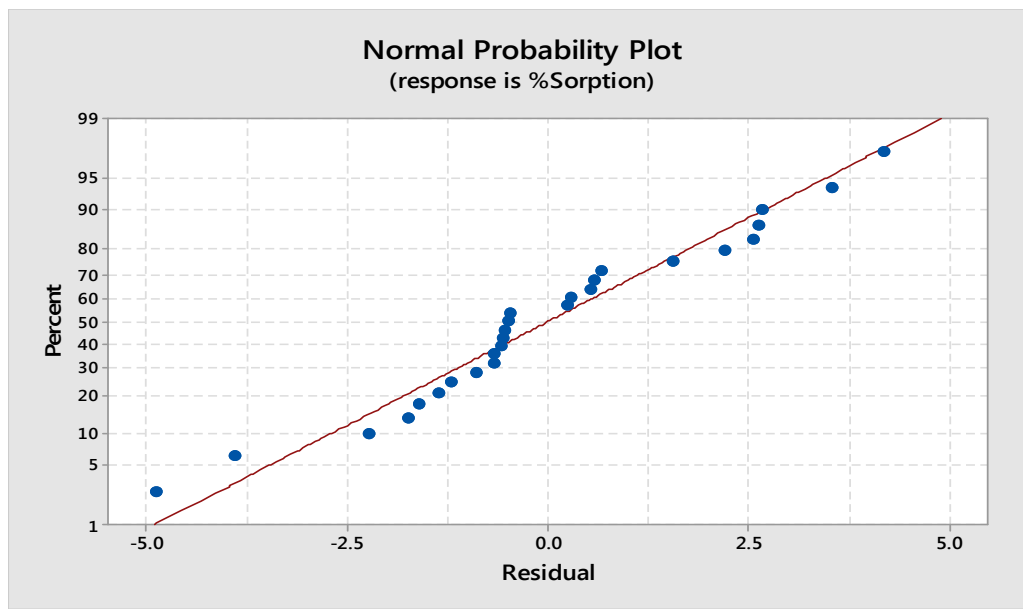


Fig 6: Normal plot of residual for the sorption of oil onto esterified ogbono shell

The Three Dimensional (3-D) response surface plots for crude oil adsorption onto fatty acid grafted ogbono shell.

The 3-D response surface and contour plots are presented in Fig 7 and 8. The 3-D response surface and contour plots are graphical representation of the interactive effects of any two variable factors. Response surface plots as a function of two factors at a time while maintaining all other factors at fixed levels are more helpful in understanding both the main and the interaction effects of these two factors. These plots as shown in fig. 7 – 8, can be easily obtained by calculating from the model, the values taken by one factor where the second varies with constraint of a given Y value. The response surface curves were plotted to understand the interaction of the variables and to determine the optimum level of each variable for maximum responses.

The nature of the response surface curves shows the interaction between the variables. The elliptical shape of the curve indicates good interaction of the two variables. From figs. 7-8, it was observed that the elliptical nature of the contour in graphs depicts the interactions of all the variables. There was a relative significant interaction between every two variables, and there was a maximum predicted yield as indicated by the surface confined in the smallest ellipse in the contour diagrams.

Temperature – Time interaction effect

The temperature –time interaction effect was plotted against oil sorption and presented as shown in fig. 7. Keeping every other factor constant, it was observed that the contour lines for the effect of temperature and time interactions were somewhat curve and circle indicating a good interaction. The contour lines showed that the interactions are significant. The significant level was proven by the p-values as shown in Table 4 which indicates that the p-values were less than 0.05. It can be concluded that increase in temperature and time, increases the rate of oil sorption by the activated biomass. The interaction of temperature and time (X_1X_2) was included in the model equation 4 for improvement of the model performance since the interactions are significant.

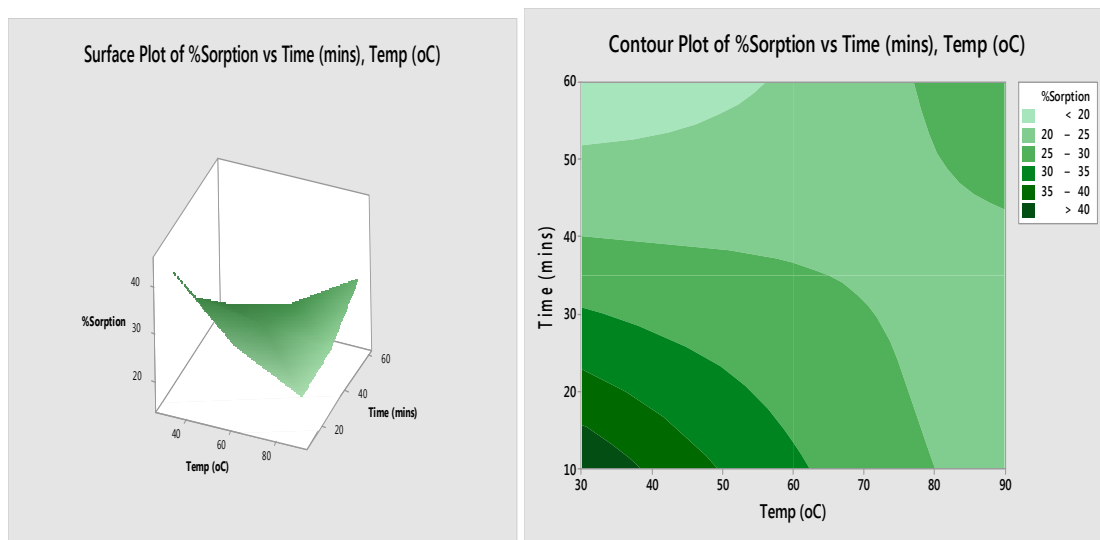


Fig 7 : Response surface and contour plots for the effect of time and temperature on sorption of oil by fatty acid grafted ogbono shell.

pH- Temperature interaction effect

The pH- temperature effect (X_2X_4) was included in equation 4 to improve the model performance. Fig 8 shows the response surface plot and contour plot for the effect of pH-temperature interaction on the percentage sorption of oil by the activated biomass. From the figure, the shape of the contour is curve showing a good interaction. The 3D plots also showed that almost equal percentage sorption could be obtained at low temperature, low pH; low

temperature, high pH; high temperature, low pH; and high temperature, high pH. The height of the 3D seems to be the same at the four edges of the curve. The p-value of the curve is less than 0.05 which indicates that the interaction is statistically significant.

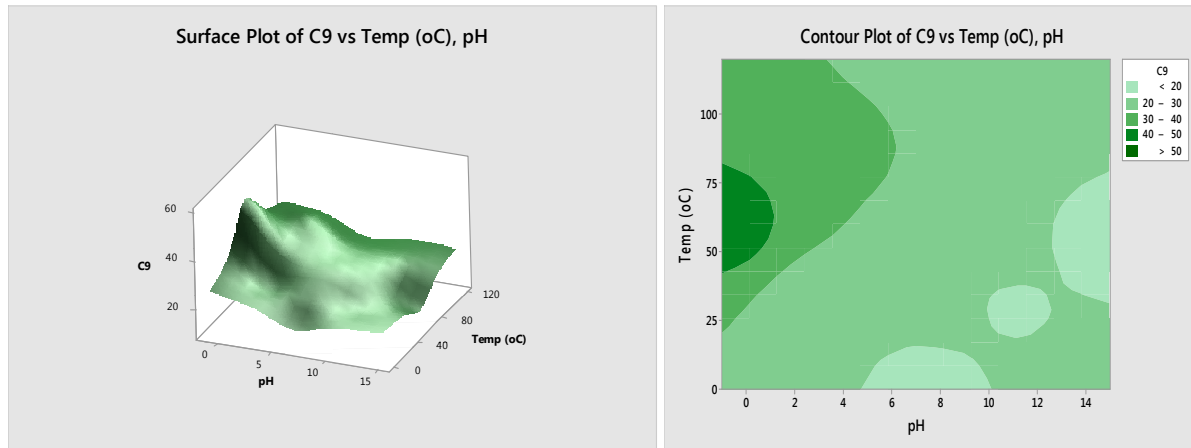


Fig 8: Response surface and contour plots for the effect of pH and temperature on soption of oil by esterified ogbono shell

The numerical optimum conditions

The developed model as shown in equation 4 for the process parameters was optimized using response optimizer facility that is available on Minitab software version 17.0 which provided several numerical optimum solutions. The optimization is also interactive and allows for the compromise among the various independent variables and responses (Yuksel et al., 2006; Yi et al., 2010). The optimum solutions are given in Table 5 including 10 min time, 60 °C temperature, 1.4g dosage, pH of 3 at the theoretical percentage removal of 78.77%. The theoretical removal percentage was verified by carrying out adsorption process using the optimum parameters. The result of the verified experiment was recorded as the actual percentage removal. The actual percentage removal was in close agreement with the theoretical value as shown in Table 5.

Table 5: The theoretical optimum solutions for esterified ogbono shell with the comparative removal percentage.

No.	Time (min)	Temp (°C)	Dosage (g)	Predicted (%R)	Actual (%R)
1	10.0	60	1.4	78.77	76.40

Conclusion

This comparative study revealed that carbonized ogbono shell modified by esterification process using steric acid can be used as an eco-friendly adsorbent for the maximum removal oil layer from oil polluted water surface. FTIR analysis of activated and uncarbonized biomass (ogbono shell) shows that they consist mainly of organic compounds such as hydroxyl group, amino group, amine, isocyanate, conjugated ketones. Surface morphological analysis of raw and esterified ogbono shell using SEM revealed that activation of the biomass increased the surface area significantly. Statistical analysis of the sorption of oil onto activated biomass such as (esterified ogbono shell) showed that the process can be modeled by central composite design with all the four variables affecting the process including time, temperature, dosage and pH statistically significant at 10 min time, 60 °C temperature, 1.4g dosage, pH of 3 with theoretical percentage removal of 78.77%.

References

- Uzoije A.P., Onunkwo A., Egwuonwu N., (2011). Crude Oil Sorption onto Groundnut Shell Activated Carbon: Kinetic and Isotherm Studies. *Research Journal of Environmental and Earth Sciences*, 3(5), 555-563
- Ali, N., El-Harbawi, M., Jabal, A., A., Yin, C.,Y.,(2012) Characteristics and Oil sorption effectiveness of kapok fibre, sugarcane bagasse and rice husks: oil removal suitability matrix. *Environmental Technology*, 33 (4), 481-486;
- Annunciado T.R., Sydenstricker T.H.D., Anuco S.C.; (2005). Experimental Investigation of Various Vegetable Fibers as Sorbent Materials for Oil Spills Marine Pollution. *Bulletin*, 50, 13040-13046
- Baars, B., J.,(2002). The wreckage of the oil tanker 'Erika'-human health risk assessment of beach cleaning, sunbathing and swimming, *Toxicology Letter*, 128 (1-3), 55-68.
- Banerjee, S., S., Joshi, M., V., Jayaram, R., V.,(2006). Treatment of oil spill by sorption technique using fatty acid grafted sawdust. *Journal of Chemosphere*, 64, 1026-1031.
- Behnood, R., Anvaripour, B., Jaafarzadeh, N., & Farasati, M., (2013). Application of natural sorbents in crude oil adsorption. *Oil and Gas Science and Technology Journal*, 2(4), 01-11.

- Sayed, S., A., Sayed, A., S., E., Zayed, A., M.,(2003). Oil spill pollution treatment by sorption on natural *Cynanchum Acutum L. Plant. Journal of Applied Sciences and Environmental Management*, 7, 63–73.
- Nwadiogbu J.O., Ajuwe V.I.E., Okoye P.A.C., (2016). Removal of Crude Oil from Aqueous Medium by Sorption on Hydrophobic Corncobs: Equilibrium and Kinetic Studies. *Journal of Taibah University for Science*, 10, 56-63.
- Choi H., Cloud R.N., (1992). Natural Sorbents in Oil Spill Clean up. *Environmental Science and Technology*, 26 (4), 772-776.
- Chung, S., Suidan, T., M. & Venosa, A., D., (2011). Partially Acetylated Sugarcane Bagasse for Wicking Oil from Contaminated Wetlands. *U.S Environmental Protection Agency Papers* 118.
- Datta S (2011). Adsorption removal of chromium (VI) from aqueous solution over powdered activated carbon: Optimization through response surface methodology. *J. Hazard. Mat*;173:135–143.
- Deschamps G., Caruel H., Borredon M.E., Bonnin C., Vignoles C., (2003). Oil Removal from Water by Selective Sorption on Hydrophobic Cotton Fibers: Study of Sorption Properties and Comparison with other Cotton Fiber-based Sorbents. *Environmental Science Technology*, 37 (5), 1013-1015.
- Adeyanju JA, Ogunlakin GO, Adekunle AA, Alawode GE, Majekolagbe OS (2016). Optimization of oil extracted from coconut using response surface methodology. *J. Chem. Pharm. Res*;8(1):374–381.
- Angelova, D., Uzonov, I., Uzonova, S., Gigova, A., Minchev, L., (2011) kinetics of oil and oil product adsorption by carbonized rice husks, *Chemical Engineering Journal*, 172(1), 306-311.
- Nwabanne J., T., & Igbokwe, P. K., (2008). Copper (II) uptake by adsorption using palmyra palm nut. *Advances in Applied Science Research*, 2(6), 166-175.
- Didem Özçimen (2012). An Approach to the Characterization of Biochar and Bio-Oil" *Bioengineering Department Yildiz Technical University, Turkey*
- Chauhan, B. and R. Gupta (2004), Application of statistical experimental design for optimization of alkaline protease production from *Bacillus sp RGR-14*. *Process Biochem.*,39, 2115-2122.

- Yuksel A., Mehmet C., Mesut Y., (2006). Determination of the optimum conditions for dissolution of magnesite with H₂SO₄ solutions. *Indian Journal of Chemical Technology*. 13, 391 – 397.
- Yi L., Yian Z., Aiqin W., (2010). Response surface methodology for optimizing adsorption process parameters for Methylene blue removal by a hydrogel composite. *Adsorption Science and Technology*, 28(10), 913 – 921.