

1 **THERMOGRAVIMETRY ANALYSIS OF EPOXY AND UNSATURATED**
2 **POLYESTER FILLED WITH SOME AGRICULTURAL WASTE OF DATES PALM**
3 **(*PHOENIX DACTYLIFERA*) AND AFRICAN ELEMI (*CANARIUM SHWEINFURTHII*)**
4 **PARTICULATE COMPOSITES**
5

6 **ABSTRACT**

7 Investigation of the thermal stability of epoxy and unsaturated polyester filled with some
8 agricultural waste of Dates palm (*Phoenix dactylifera*) and African elemi (*Canarium*
9 *shweinfurthii*) pits particulate composites has been conducted at a heating rate of 10°C/min using
10 thermogravimetric analysis (TGA). The study showed that the composites can withstand
11 temperature up to 340°C in inert atmosphere before decomposition and thus had good thermal
12 stability as increased in temperature had little effect on the composites before the onset of
13 degradation. The results show that the composites prepared from both fillers showed high
14 thermal stability because onset of degradation of date palm pits/epoxy (DTP/EP) commenced at
15 about 340°C which was **unusual** for lignocellulosic material while atili pits/ unsaturated polyester
16 (ATP/UP) was 320°C. Literatures have shown that most **lignocellulosic** filler degrades at their
17 processing temperature below 250°C. Thus, both fillers could be used in engineering plastics.
18

19 **Keywords:** Temperature, Thermal Stability, Degradation, Lignocellulosics
20


21 **1 INTRODUCTION**

22 Thermosetting resins are the most widely used resins in composites. The main characteristic of
23 thermosets (literally setting under heat) is that they require curing, in which they undergo a
24 molecular cross-linking process which is irreversible and renders them infusible. They therefore
25 offer high thermal stability, good rigidity and hardness, and resistance to creep. This also means
26 that, once cured, the resin and its laminate cannot be reprocessed except by methods of chemical
27 breakdown, which are currently under development. For practical purposes, therefore, cured
28 thermosetting resins can be recycled most effectively if ground to fine particles, when they can
29 be incorporated into new laminates or other products as fillers [1,2].

30 Thermosetting resins have little use on pure resin, but require addition of other chemicals to
31 render them process able. For reinforced plastics, the compounds usually comprise a resin
32 system (with curing agents, hardeners, inhibitors, plasticisers) and fillers and /or reinforcement.
33 The resin system provides the 'binder,' to a large extent dictating the cost, dimensional stability,
34 heat and chemical resistance, and basic flammability. The reinforcement can influence these
35 (particularly heat and dimensional stability) but the main effect is on tensile strength and
36 toughness. High performance fibres, of course, have a fundamental influence on cost [3,4,5].

37 Special fillers and additives can influence mechanical properties, especially for improvement
38 in dimensional stability, but they are mainly used to confer specific properties, such as flame
39 retardancy, ultraviolet (UV) stability or electrical conductivity [6]. Thermoset was the first

40 organic resins used for composites making and they still represent around two-thirds of the
41 overall composites market and about the same fraction of the overall market value as represented
42 in Fig. 1.

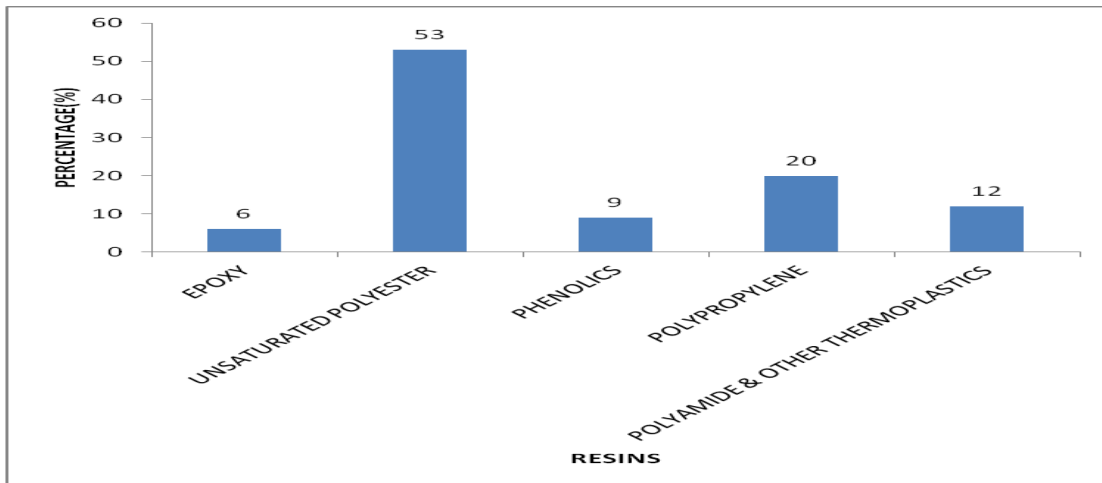

43 **FIG. 1** The overall composite market uses showing about two-thirds thermosetting resins and
44 one-third thermoplastics as matrix materials [7].
45
46

47 The plastics industry produces far more thermoplastics than it does thermosetting plastics,
48 approximately in the ratio of 4:1; however, this ratio is not maintained in the area of composite
49 materials which represent about 3 % of the total plastics industry. Approximately twice as much
50 thermosetting matrix material is used for composites than thermoplastics matrix material [7].
51

52 **1.1 Dates Palm Fruits-** Dates palm fruits consist of three main parts: date flesh, date pit, and
53 skin. That is, it is a drupe, an indehiscent fruit in which an outer fleshy part (exocarp, or skin;
54 and mesocarp, or flesh) surrounds a shell (the pit, stone, or pyrene) of hardened endocarp. The
55 main sugars of date flesh are glucose, fructose and sucrose. At early stages of maturing the fruit,
56 it has a high content of sucrose, but during the maturation process it is converted to glucose and
57 fructose [8]. It contains a single seed (kernel) about 2–2.5 cm long and 6–8 mm thick. The kernel
58 is a major by-product of the date palm-processing industry. They contained 7.1–10.3 % moisture,
59 5.0–6.3 % protein; 9.9–13.5 % fat; 46–51 % acid detergent fibre; 65–69 % neutral detergent
60 fibre; and 1.0–1.8 % ash. Date pit is mainly used as animal feed [9].
61
62



63 **PLATE 1** Dates palm raw fruits and stony pits
64

65 **1.2 African elemi (Atili)-**. It is one of the tropical trees whose fruits contain oils in its pulp and
66 seed kernel. The pulp is of oily consistency and edible. It is a drupe with an outer skin (exocarp),
67 a 3 mm layer of fleshy mesocarp that is the edible portion and a hard (five-sided, 2 cm long and
68 1 cm wide) stony endocarp (pit) surrounding the tiny seed kernel that is edible. The endocarp (pit
69 or stone) is thrown away after the fleshy part is eaten. In some culture, the pits are strung into
70 necklaces or attached to traditional instruments, and in some cases used as local beads for feet
71 [10].



72
73
74 **PLATE 2** African elemi (Atili) fruits, and stony pits
75

76 The research is aim at investigating the thermal stability of thermosets (epoxy and unsaturated
77 polyester) composite prepared with fillers from some agricultural wastes.
78

79 **2 MATERIALS AND METHODS**

80 **2.1 Materials-** Thermogravimetric Analyzer (TGA Q500 V20.13 Build 39) by Mettler Toledo;
81 Date palm fruits, aluminium foil, Epoxy Resin (commercially available epoxy resin (3554A) of
82 density 1.17 g/cm³) and polyamine amine (Hardener3554B) of density 1.03 g/cm³ were procured
83 from a local supplier in Ojota, Lagos, Nigeria. The date palm fruits and African elemi (Atili)
84 fruits were obtained from Gwagwalada market, F.C.T; Nigeria.

85 **2.2 Methods**

86 **2.2.1 Filler Preparation-** The date pits (DTP) and African elemi or atili pits (ATP) were
87 separated from their fruits manually, thereafter; they were washed and cleaned to remove
88 contaminants. They were then dried and grounded with hammer mill to obtain filler powder. The
89 fillers were made to pass through wire mesh screen to obtain different particle sizes of 150 µm
90 The fillers were then oven dried for 24 hrs at temperature of about 70 °C before use so as to
91 reduce the moisture content. Samples were thereafter stored in a sealed container prior to
92 compounding.

93 **2.2.2 Compounding-** Five levels of filler loading (10, 20, 30, 40, & 50 wt %) were made from
94 fillers with the matrixes (epoxy and unsaturated polyester). Neat resins without filler were
95 equally prepared to serve as control.
96

97 **2.2.2.1 Date and Atili pits Epoxy Composites (DTP/EP and ATP/EP)-** The composites with
98 varying degrees of filler percentage (i.e. 0, 10 wt%, 20 wt%, 30 wt%, 40 wt% and 50 wt%) were

99 prepared. This was achieved by mixing the various ratios of the prepared fillers with the epoxy to
100 form homogenous blends. The mixing was achieved via manual stirring method for 10 minutes.
101 The volume ratio of resin to hardener was 2:1, and after thorough mixing with the filler, the resin
102 was poured onto the cavity of glass mould of dimensions 160 mm x 70 mm x 4.5 mm overlaid
103 with aluminium foil so as to serve as releasing agent. The mixture was allowed to cure at room
104 temperature for 24 hours before removal from the mould.

105

106 **2.2.2.2 Date and Atili pits unsaturated polyester composites (DTP/UP and ATP/UP)-**
107 .Unsaturated polyester composites with varying degrees of filler percentage ((i.e. 0, 10 wt%, 20
108 wt%, 30 wt%, 40 wt% and 50 wt%)) were also prepared. This was achieved by mixing the
109 various ratios of the prepared fillers and the unsaturated polyester resin to form homogenous
110 blends. The mixing was achieved via manual stirring method for 7 minutes. For example, 10 %
111 filler loading was prepared by adding 0.2 % of the accelerator cobalt naphthenate to mixture of
112 resin and the filler and stirred for 3 minutes before the final addition of the catalyst i.e methyl
113 ethyl ketone peroxide in ratio 2 % of the resin, the mixture was poured onto the cavity of glass
114 mould overlaid with aluminium foil so as to serve as releasing agent. The mixture was allowed to
115 cure at room temperature for 24 hours before removal from the mould. The composites were kept
116 for 20 days at room temperature for complete curing.


117

118 **2.3 Thermogravimetric Analysis-** The thermogravimetric analysis (TGA) was performed on
119 the date pits/epoxy (DPT/EP 1), date pits/ unsaturated polyester (DTP/UP), atili pits/epoxy
120 (ATP/EP), atili pits/unsaturated polyester (ATP/UP) composites using TGA Q500 machine. The
121 Samples were subjected to pyrolysis in nitrogen environment to a maximum temperature of 900
122 °C at a heating ramp rate of 10 °C/min. The weight loss was recorded in response to increasing
123 temperature, with final residue yield on set of degradation temperature.

124 **3 RESULTS**


125 The results of the thermogravimetry conducted are as presented in Figures 2 to 7.

126

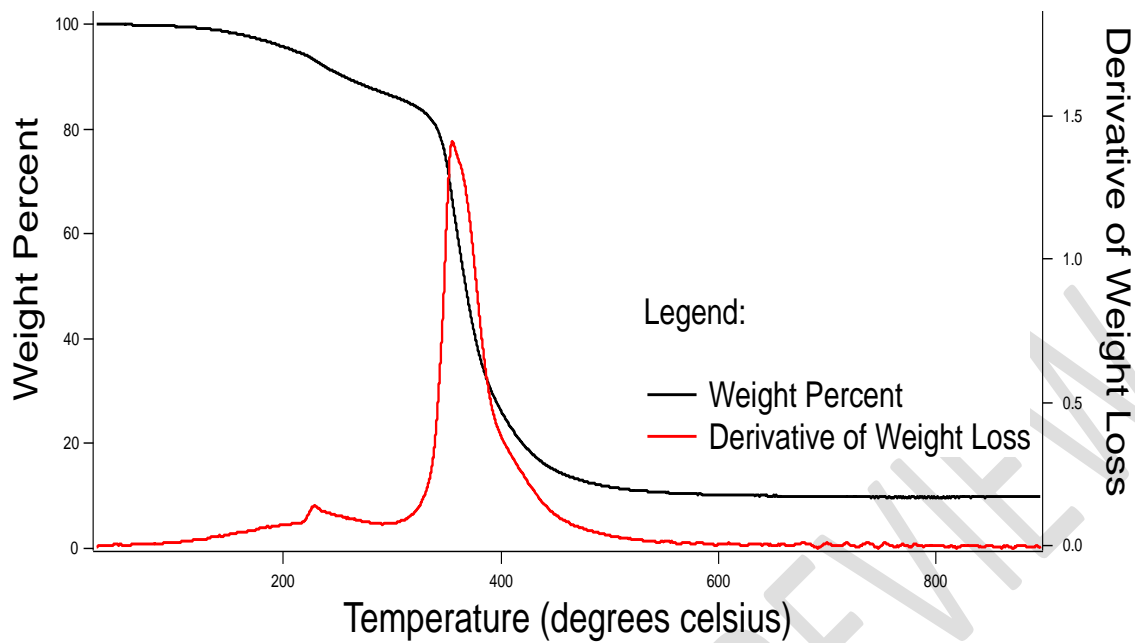

127


128 **FIG. 2** Thermogravimetric analysis (TGA) and **derivate graphic** analysis curves of the neat
 129 epoxy resin (EP)

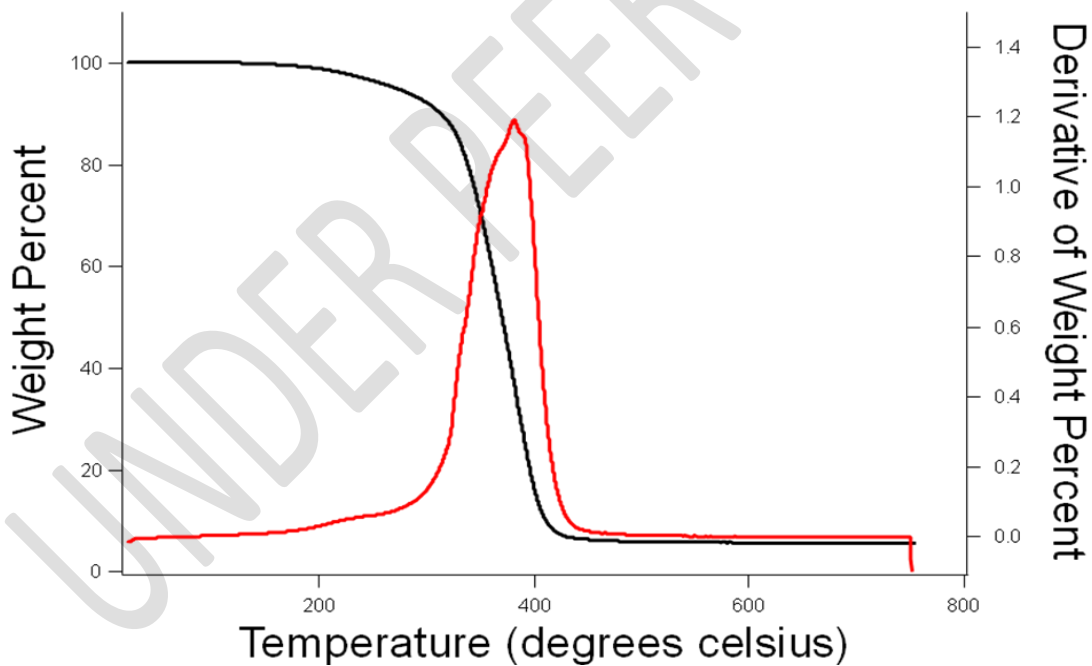

130


131 **FIG 3** Thermogravimetric analysis (TGA) and **derivate graphic** analysis curves of neat
 132 unsaturated polyester (UP).

133

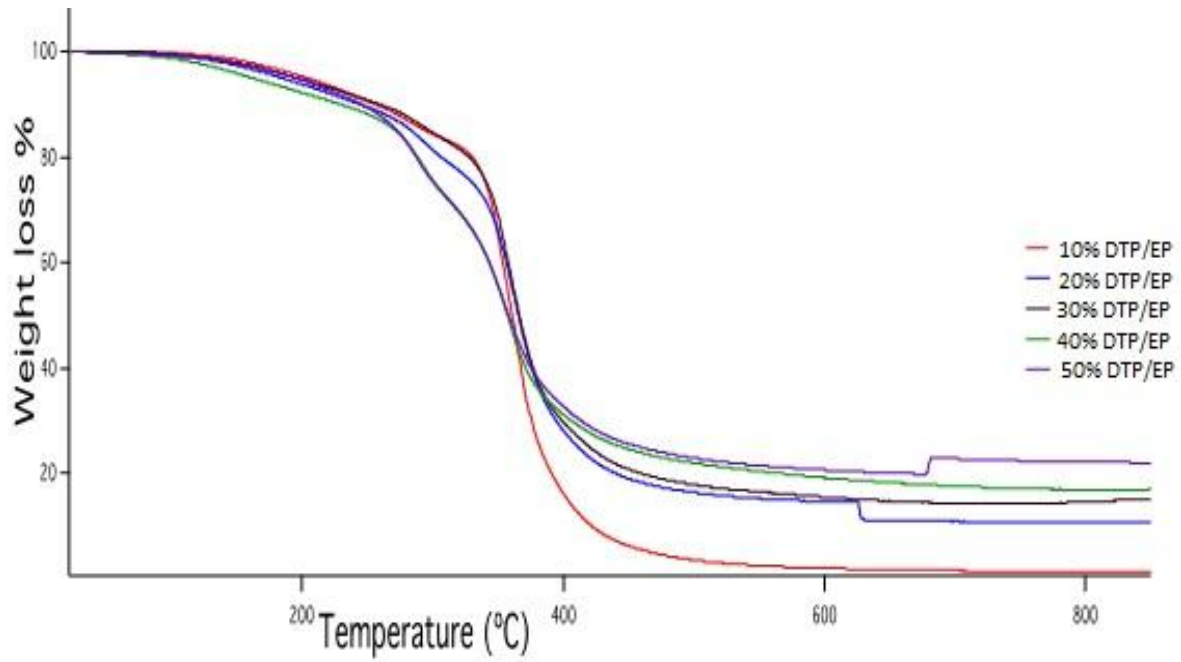

134


135 **FIG. 4** Thermogravimetric analysis (TGA) analysis curves of date pits filled epoxy (DTP/EP 1)
 136 composites

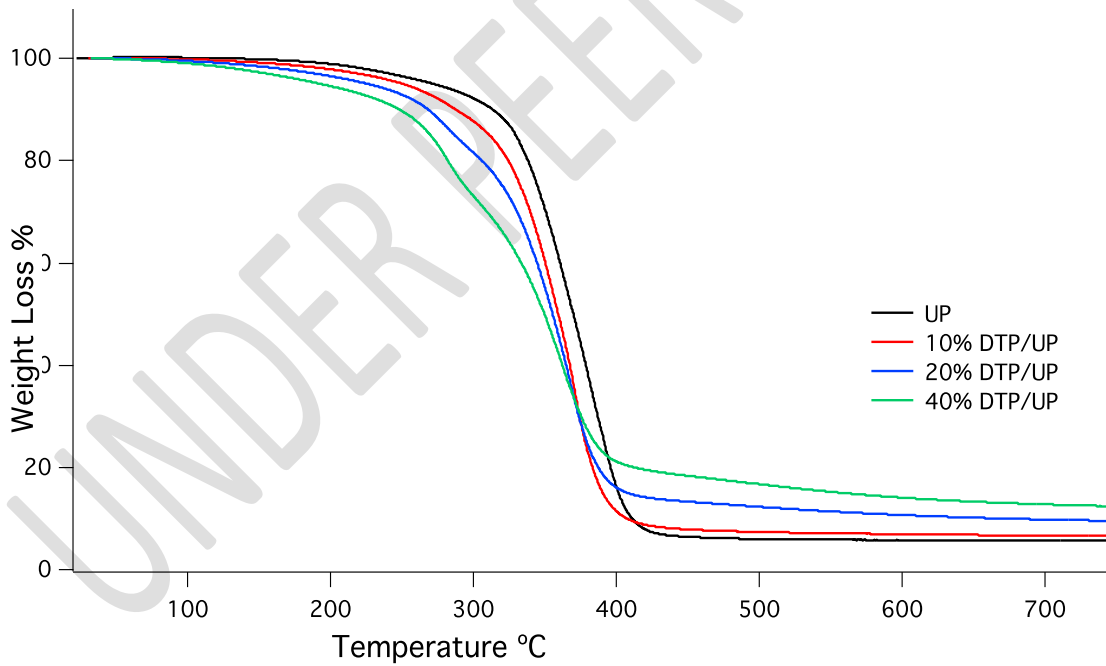

137

138


139 **FIG. 5** Thermogravimetric analysis (TGA) analysis curves of date pits filled (DTP/UP) filled
 140 unsaturated polyester composites.

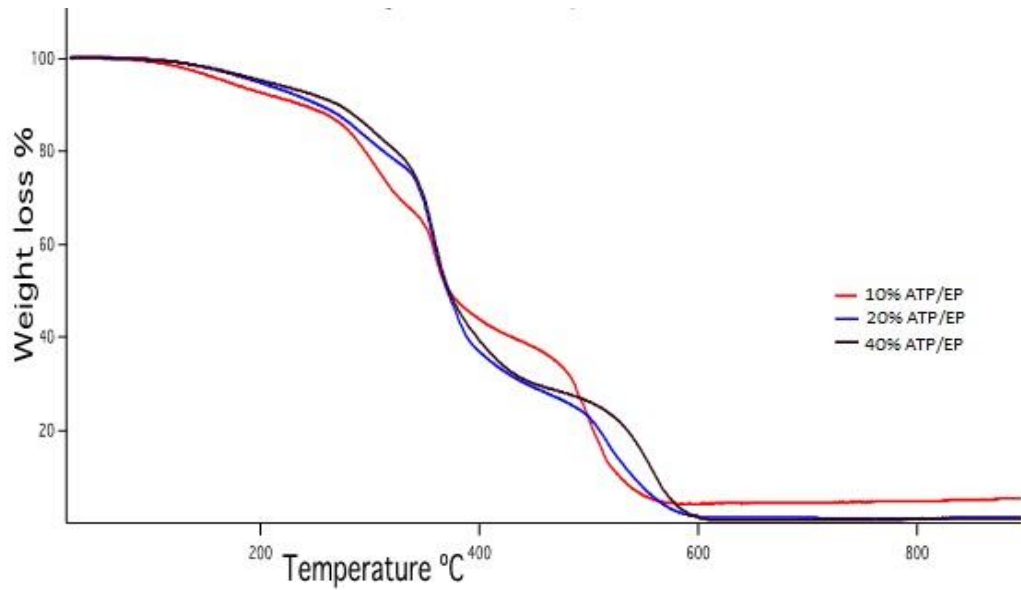

141

142 **FIG. 6** Thermogravimetric analysis (TGA) analysis curves of atili pits filled epoxy (ATP/EP)
 143 composites.

144

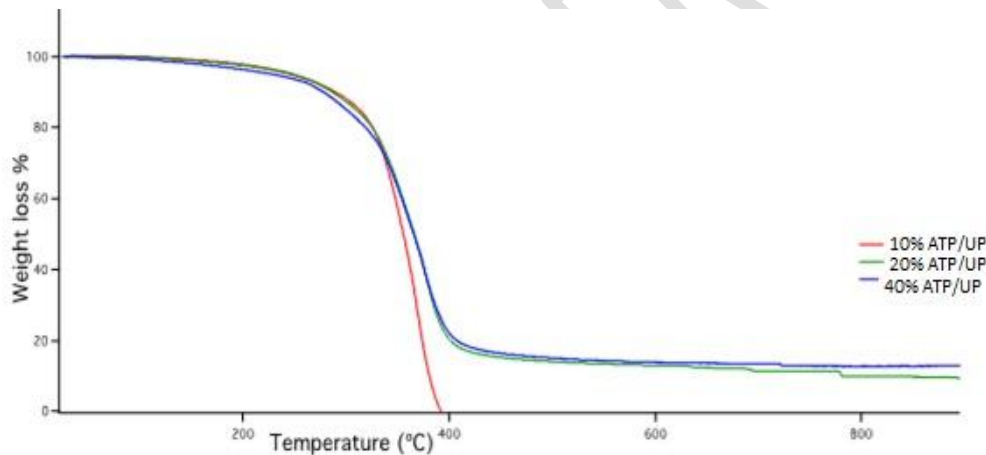

145

146 **FIG. 7** Thermogravimetric analysis (TGA) analysis curves of Atili filled unsaturated polyester
 147 (ATP/UP) composites.

148 **4 DISCUSSIONS**

149 Figure 2 shows the thermogravimetric curve of the unfilled epoxy resins. The results show a
 150 single step decomposition pattern. However, a gradual mass- loss of about 0.4% at 100 °C was
 151 observed, while at 130°C, the resin lost 0.91% of its mass and this can be traced to loss of

152 moisture content of the material. Shortly before the onset of decomposition temperature, the
153 resin lost 9.3% of its mass due to loss of occluded water and other component at temperature of
154 250°C. Onset of decomposition commenced at about 340°C till the final decomposition
155 temperature of about 420°C in which 80 % of the material mass have been lost. At 500°C the
156 mass loss was 88.2% while at 600, 650 and 700°C, the mass loss was 90% meaning that the
157 material must have experience total decomposition leaving 10% residue or ashes.

158 Figure 3 shows the thermogravimetric analysis of the unfilled unsaturated polyester resins and a
159 single step decomposition pattern can be observed. However, unlike epoxy which experienced a
160 gradual mass- loss of about 18% before the onset of decomposition, unsaturated polyester shows
161 minimal loss in weight before the onset of decomposition temperature. That is, unsaturated
162 polyester was more stable than epoxy at temperature below 100°C, this is because unsaturated
163 polyester recorded no loss in mass and this was confirmed by the low moisture content. At 130
164 °C, the resin lost only 0.02 % of its weight compares to epoxy with value 0.91% at the same
165 temperature. Shortly before the onset of decomposition temperature, the resin lost only 3.5% of
166 its mass due to loss of bounded water and other component at temperature of 250°C. Onset of
167 decomposition commenced at about 317°C till the final decomposition temperature of about 400
168 °C in which 92% of the material weight have been lost. At 500, 600, 650 and 700°C, the mass
169 loss was 94% meaning that the material must have experience total decomposition leaving 6 %
170 residue. From the result in Figure 2 and 3, epoxy is more thermally stable than unsaturated
171 polyester.

172 Figure 4 shows the TGA curve of date pits filled epoxy (DTP /EP) composites at filler loading of
173 10 wt% to 50 wt%, it can be seen that the 40 wt% and 50 wt% DTP/epoxy composites lost their
174 weight earlier than the other samples. This is attributed to the high moisture content of the filler
175 due to hydrophilic nature of lignocellulosic filler at higher filler loading. The percentage of
176 weight reduction at 500°C of 50 wt% filler loading was 78% which mean about 22% of residues
177 left after the composites were degraded. From the results shown in Figure 3 it can also be seen
178 that 10 % date pits filled epoxy (DTP/EP) composite has the lowest residue due to the absence of
179 char followed by 20 wt% DTP/EP composites. Lignin in filler is responsible for charring thus 40
180 wt% and 50 wt% DTP/EP composite will have more char [11]. Thus, the higher the filler
181 content, the higher the residue after decomposition. The onset of decomposition temperature of
182 10 wt% DTP/EP composite started around 310 °C and lasted till the decomposition temperature
183 of 441°C while that of 50 wt% DTP/EP composite was observed at 281°C and lasted till 444°C.
184 Thus, the ash content of the composites increased as the filler loading increases. The 10 %
185 DTP/EP seems to be more thermally stable when compared to other composites since it shows
186 less variation in weight as the temperature increases. Some researchers have found that the
187 addition of natural fibres causes reduction in the thermal stability of the composite due to the
188 influence of the less stable fibres [12]. It was equally observed from the result that the epoxy
189 filled 10 wt% date pits (DTP/EP) composite experienced mass-loss of 16.7% at the onset of

190 decomposition temperature (310°C) while 0.5% was lost at 130°C. At 500°C, the mass – loss for
191 10 wt%, 40 wt%, and 50 wt% are 96, 77.03 and 77.6%, respectively.

192 Fig. 5 shows the TGA for date pits filled unsaturated polyester (DTP/UP) composites. It can
193 be seen that the filler followed similar pattern in unsaturated polyester with that of epoxy
194 composites in Fig. 4, except that the DTP/UP composites experienced high degree of stability at
195 temperature below 13°C.

196 That is, unsaturated polyester was more stable than epoxy at temperature below 100°C, this is
197 because unsaturated polyester recorded no loss in mass. At 130°C, the unfilled unsaturated
198 polyester (UP) lost only 0.02% of its weight compares to the unfilled epoxy with value 0.91 % at
199 the same temperature. The 10 wt%, 20 wt%, and 40 wt% date filled unsaturated polyester,
200 respectively, lost: 0.35%, 0.7% and 0.89% of their mass at 100°C, and at 130°C, 0.6%, 0.91%,
201 and 1.7 % mass was lost, respectively. At the decomposition temperature of about 420°C, the
202 char left for the respective 10 wt%, 20 wt%, and 40 wt% date filled unsaturated polyester
203 composites are 17%, 32% and 21% respectively.

204 Fig. 6 shows the thermogravimetric curve of atili pits/ epoxy (ATP/EP) composites. The
205 results seem to be different from the pattern of curve shown in Figure 4 and 5. The graph shows
206 multiples steps of decom position which might be due to non consistency in filler – matrix
207 interaction. The 10%, 20%, and 40% atili filled epoxy composites respectively lost 2.3, 1.0 and
208 1.1% at 130°C, while at 400°C, the mass-loss was 56, 63 and 61% as it can be seen from Fig. 6.

209 Fig. 6 also shows the decomposition pattern of Atilio pits filled unsaturated polyester
210 (ATP/UP) composites. A single stage decomposition step was seen, in which 10 wt% atili pits
211 unsaturated polyester (ATP/UP) showed more thermal stability than 20 wt% and 40 wt% Atilio
212 pits unsaturated polyester (ATP/UP) composites. The 10 wt% gave no residue after
213 decomposition at about 400°C. It can be observed from Figure 7 that the onset of decomposition
214 for 10 wt% and 20 wt% atili pits unsaturated polyester (ATP/UP) is at 298°C and 242°C,
215 respectively, while the final combustion temperature is 400°C and 405°C respectively. The 40
216 wt% filler loading left more char after combustion than 20 wt% filler loading as expected due to
217 higher lignin content. The initial weight loss of 0.6%, 0.8% and 1.44% for 10 wt%, 20 wt% and
218 40 wt% filler ratio respectively was observed for the sample at about 130°C while the unfilled
219 unsaturated polyester gave 0.02 % loss of weight at the same temperature. The initial mass–loss
220 can be attributed to loss of moisture content at that temperature indicating the higher the filler
221 loading, the higher will be the percentage loss of moisture. This is due to the hydrophilic nature
222 of the filler.

223 At the onset of degradation, 10 wt%, 20 wt% and 40 wt% ATP/UP composites lost 11.42%,
224 4.5% and 6.6% of their weight while 99%, 82% and 80% was lost at the decomposition
225 temperature of 400°C, 405°C and 413°C, respectively.

226 **CONCLUSIONS**

227 Thermogravimetric analysis of composites prepared from both fillers showed appreciable
228 thermal stability. Literatures have shown that most lignocellusics filler degrades at their
229 processing temperature of below 250°C [3, 8, 7]. Thus, both fillers could be used with thermosets
230 to produce composites that will be of use for both outdoor materials and in engineering plastics
231 where such thermal stability is required.

232

233 **REFERENCES**

- 234 1. Katchy, E.M. (2000). Principles of Polymer Science. El'Demak Publishers. 1st Ed. pp
235 326- 340.
- 236 2. Joel, R.F., (2003). Polymer Science & Technology. Prentice- Hall Inc, 2nd ed. pp 3-
237
- 238 3. Ibrahim, M.S., Sapuan, S.M., and Faieza, A.A., (2012). Mechanical and Thermal
239 Properties of Composites from Unsaturated Polyester Filled With Oil Palm Ash. *Journal*
240 *of Mechanical Engineering and Sciences (JMES)*, 2:133-147.
- 241 4. Aranjó J.R., Waldman W.R. and De Paoli M.A. (2008). Thermal Properties of High
242 Density Polyethylene Composites with Natural Fibres: Coupling agent effect. *Polymer*
243 *Degradation and stability*, 93: 1770 - 1775.
- 244 5. Rowell R.M. (2000). Effect of steam pre-treatment of jute fibre on dimensional stability
245 of jute composite. *Journal of applied Polymer Science*, 76, 1652 - 1661.
- 246 6. Chirinos-Padron, A.J., and Allen, N.S.,(1992) “Handbook of polymer degradation”, (ed.
247 S.H. Hamidet al.), Chapter 8, Marcel Dakker, New York, pp. 261-303.
- 248 7. Bunsell, A.R. and Renard, J. (2005). Fundamentals of Fibre Reinforced Composite
249 Materials. Institute of Physics Publishing Bristol and Philadelphia.
- 250
- 251 8. Marzieh, S., Keikhosro, K., and Mohammad, J.T., (2010). Palm Date Fibres: Analysis
252 and Enzymatic Hydrolysis. *Int. J. Mol. Sci.* 11 : 4285-4296;
- 253 9. Hamada, J.S., Hashim, I.B., Sharif, F.A. (2002). Preliminary analysis and potential uses of
254 date pits in foods. *Food Chemistry* 76 :135–137
- 255 10. Burkill, H.M. (1994). *Useful plants of west tropical Africa*. Vol. 2. Families E-I. Kew:
256 Royal Botanical Gardens. Pp 648.
- 257 11. Fuad, M.Y.A., Rahmad, S., and Azlan, M.R.N., (1998). Filler Content Determination Of
258 Bio- Based Thermoplastics Composites By Thermogravimetric Analysis“ Proceedings of
259 the Fourth International Conference on Advances in Materials and Processing
260 Technologies, Kuala Lumpur. Pp 268-275.

261
262
263
264
265

12. Luo, S., and Netravali, A.N., (1999). “Mechanical And Thermal Properties of Environmentally Friendly “Green” Composites Made from Pineapples Leaf Fibres And Poly (Hydroxybutynate-Co-Valerate) Resin”, *Polymer Composites*, 20 (3) : 367-378.

UNDER PEER REVIEW